

## [Ag-20S2P(OR)(2)(12)]: A Superatom Complex with a Chiral Metallic Core and High Potential for Isomerism

Rajendra S. Dhayal, Yan-Ru Lin, Jian-Hong Liao, Yuan-Jang Chen, Yu-Chiao Liu, Ming-Hsi Chiang, Samia Kahlal, Jean-Yves Saillard, C. W. Liu

### ► To cite this version:

Rajendra S. Dhayal, Yan-Ru Lin, Jian-Hong Liao, Yuan-Jang Chen, Yu-Chiao Liu, et al.. [Ag-20S2P(OR)(2)(12)]: A Superatom Complex with a Chiral Metallic Core and High Potential for Isomerism. Chemistry - A European Journal, Wiley-VCH Verlag, 2016, 22 (29), pp.9943–9947. 10.1002/chem.201602275 . hal-01357410

HAL Id: hal-01357410

<https://hal-univ-rennes1.archives-ouvertes.fr/hal-01357410>

Submitted on 17 Feb 2017

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire HAL, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

## [Ag<sub>20</sub>{S<sub>2</sub>P(OR)<sub>2</sub>]<sub>12</sub>]: A Superatom With Chiral Metallic Core and Rich Isomerism Potentialities\*\*

Rajendra S. Dhayal, Yan-Ru Lin, Jian-Hong Liao, Yuan-Jang Chen, Yu-Chiao Liu, Ming-Hsi Chiang, Samia Kahlal, Jean-Yves Saillard\* and C. W. Liu\*

---

[\*] Dr. R. S. Dhayal, Y.-R. Lin, J.-H. Liao, Prof. C. W. Liu  
Department of Chemistry, National Dong Hwa University  
No. 1, Sec. 2, Da Hsueh Rd., Shoufeng, Hualien 97401, Taiwan, R.O.C.  
Fax: (+886)3-863-3570  
E-mail: chenwei@mail.ndhu.edu.tw  
Homepage: <http://faculty.ndhu.edu.tw/~cwl/index.htm>

Dr. R. S. Dhayal

Centre for Chemical Sciences, School of Basic and Applied Sciences, Central University of Punjab, Bathinda-151 001, India

Dr. S. Kahlal, Prof. J.-Y. Saillard

UMR-CNRS, 6226 "Institut des Sciences Chimiques de Rennes", Université de Rennes 1, 35042 Rennes Cedex, France.

Dr. Y.-C. Liu, Dr. M.-H. Chiang

Institute of Chemistry, Academia Sinica, Taipei, Taiwan, R.O.C.

Prof. Y.-J. Chen

Department of Chemistry, Fu Jen Catholic University, New Taipei City 24205, Taiwan, R. O. C.

[\*\*] This research was supported by the Ministry of Science and Technology of Taiwan (MOST 103-2113-M-259-003). The French national computer centers GENCI-CINES and GENCI-IDRISS are acknowledged for computational resources (grant 2015-087367). Metrical parameters for the structure of compounds are available free of charge from the Cambridge Crystallographic Data Centre under reference nos. CCDC 1454778 (**2**), 1454779(**3**).

---

### Abstract

Herein we present the synthesis and the first structural determination of a silver nanocluster [Ag<sub>20</sub>{S<sub>2</sub>P(O<sup>i</sup>Pr)<sub>2</sub>]<sub>12</sub>, **2**, which contains an intrinsic chiral metallic core and is produced via reduction of one silver ion from the eight-electron superatom [Ag<sub>21</sub>{S<sub>2</sub>P(O<sup>i</sup>Pr)<sub>2</sub>]<sub>12</sub>(PF<sub>6</sub>), **1**, by borohydrides. Single crystal X-ray analysis displays an Ag<sub>20</sub> core of pseudo C<sub>3</sub> symmetry comprising a silver-centered Ag<sub>13</sub> icosahedron capped by seven silver atoms. Its n-propyl derivative, [Ag<sub>20</sub>{S<sub>2</sub>P(O<sup>n</sup>Pr)<sub>2</sub>]<sub>12</sub> (**3**), can also be prepared by the treatment of silver(I) salts and dithiophosphates in a stoichiometric ratio in the presence of excess amount of [BH<sub>4</sub>]<sup>-</sup>. Astonishingly crystal structure analyses reveal that the capping silver-atom positions relative to their icosahedral core are distinctly different in **2** and **3** and generate isomeric, chiral Ag<sub>20</sub> cores. Both Ag<sub>20</sub> clusters display an emission maximum in the near IR region. DFT calculations are consistent with a description within the superatom model of an 8-electron [Ag<sub>13</sub>]<sup>5+</sup> core protected by a [Ag<sub>7</sub>{S<sub>2</sub>P(OR)<sub>2</sub>]<sub>12</sub><sup>5-</sup> external shell. Moreover, two additional structural variations are predicted by DFT, showing isomerism potentialities for such [Ag<sub>20</sub>{S<sub>2</sub>P(OR)<sub>2</sub>]<sub>12</sub> species.

Atomically precise noble metal nanoclusters of which structures were determined by single crystal X-ray diffraction have been very challenging to pursue, due to difficulties in the growth of single crystals of appropriate quality. However, owing to their potential applications in multidisciplinary fields such as catalysis, luminescence, sensing, electronics, and biology,<sup>[1-3]</sup> they remain highly topical. In the past few years, significant progresses have been made in the single-crystal structure study of gold nanoclusters<sup>[3]</sup> protected by Au-thiolate staple units, such as Au<sub>102</sub>,<sup>[4]</sup> Au<sub>133</sub>,<sup>[5]</sup> Au<sub>38</sub>,<sup>[6]</sup> Au<sub>36</sub>,<sup>[7]</sup> Au<sub>30</sub>,<sup>[8]</sup> Au<sub>28</sub>,<sup>[9]</sup> and Au<sub>25</sub>.<sup>[10]</sup> Among these clusters, the Au<sub>102</sub>, Au<sub>38</sub>, and Au<sub>28</sub> cores are chiral due to asymmetric arrangement of the Au-thiolate staple units. A chiral Au<sub>20</sub> core of C<sub>3</sub> symmetry was also revealed in [Au<sub>20</sub>(PP<sub>3</sub>)<sub>4</sub>]Cl<sub>4</sub> (P = tetradentate phosphine), which consists of a centered-icosahedral Au<sub>13</sub> capped by seven Au atoms in a helical Y-shape.<sup>[11]</sup> Besides the aforementioned investigations, the structural isomerism study at nanoscale in Au<sub>28</sub>(SR)<sub>20</sub> (R = -c-C<sub>6</sub>H<sub>11</sub>, -Ph-<sup>t</sup>Bu)<sup>[12]</sup> has opened up an exciting new avenue for nanostructure researches. Even though isomers lying close in energy have been predicted in Ag clusters based on DFT study,<sup>[13]</sup> structurally characterized isomeric silver nanoclusters remain unknown.

The structural diversity identified in gold nanoclusters inspires scientists to develop silver analogues. The unusual stability of the M<sub>4</sub>Ag<sub>44</sub>(SPh)<sub>30</sub> (M = alkali metal) nanoclusters<sup>[14]</sup> was attributed to an 18-electron superatomic closed-shell configuration. More recently, Bakr *et al.* reported the structures of [Ag<sub>25</sub>(SR)<sub>18</sub>]<sup>-</sup> and [Ag<sub>29</sub>(BDT)<sub>12</sub>(TPP)<sub>4</sub>], where an Ag<sub>25</sub> structure was found virtually identical to that of [Au<sub>25</sub>(SR)<sub>18</sub>].<sup>[15]</sup> Subsequently there were reports on doped thiolate silver nanoparticles, [MAg<sub>24</sub>(SR)<sub>18</sub>]<sup>2-</sup> (M = Pt, Pd)<sup>[16]</sup> and [AuAg<sub>24</sub>(SR)<sub>18</sub>].<sup>[17]</sup> Interestingly, intercluster reactions between Au<sub>25</sub>(SR)<sub>18</sub> and [Ag<sub>44</sub>(SR)<sub>30</sub>]<sup>4+</sup> reveals the formation of [Au<sub>25-x</sub>Ag<sub>x</sub>(SR)<sub>18</sub>] (x = 0-20), which are primarily characterized by mass spectrometry.<sup>[18]</sup> However to the best of our knowledge *there has been no reported structural evidence on a superatom-type silver nanocluster having a chiral inorganic core*. Indeed, nanoscale chirality is of immense interest due to varieties of applications such as enantioselective catalysis, chiro- optical devices, *etc.*<sup>[19, 20]</sup>


Our group has a strong interest in pursuit of group 11 nanoparticle formation pathways made via wet chemical reduction methods. Along this direction, we have successfully characterized several copper hydrides stabilized by bidentate dichalcogen (S/Se) ligands (L)<sup>[21]</sup> as well as hydrido silver (or copper) clusters en route to the ultimate metal nanoparticles from which assumptions on the existence of various alloy clusters as key intermediates were proposed.<sup>[22]</sup> Eventually, the first eight-electron silver nanocluster [Ag<sub>21</sub>{S<sub>2</sub>P(O<sup>i</sup>Pr)<sub>2</sub>]<sub>12</sub>(PF<sub>6</sub>), **1**,<sup>[23]</sup> was isolated in the series. Bearing in mind that a chiral superatom may be produced through removal of one peripheral silver ion from the Ag<sub>21</sub> core of **1**, we report herein the new [Ag<sub>20</sub>{S<sub>2</sub>P(O<sup>i</sup>Pr)<sub>2</sub>]<sub>12</sub> cluster, **2**, that is merely one silver atom smaller than the previous Ag<sub>21</sub> cluster. The new Ag<sub>20</sub> cluster core, which exhibits interesting differences in structural features and optical properties from those of the Ag<sub>21</sub> cluster, consists of an intrinsic chiral inorganic core, a combination of a centered-icosahedral Ag<sub>13</sub> nucleus and seven capping silver atoms, to retain eight electrons in agreement with the unified superatom concept.<sup>[24]</sup>

The initial synthesis of pure [Ag<sub>20</sub>{S<sub>2</sub>P(O<sup>i</sup>Pr)<sub>2</sub>]<sub>12</sub>, **2**, which is air- and moisture-stable, started with [Ag<sub>21</sub>{S<sub>2</sub>P(O<sup>i</sup>Pr)<sub>2</sub>]<sub>12</sub>(PF<sub>6</sub>), **1** by dissolving it in tetrahydrofuran (THF) (see supporting information). The resulting solution was cooled to -20 °C for 20 minutes and NaBH<sub>4</sub> solution (a mixture of DMF and THF in a 1:4 ratio) was then added quickly. After 1h, solvents were removed under reduced pressure and the obtained brown-red solid was extracted in sufficient amount of hexane. The fractions of hexane were combined and dried to yield pure **2**. Alternatively, a direct synthesis of **2** was developed by treating Ag<sup>+</sup> salts and dithiophosphates (dtp) in stoichiometric ratios in the presence of excess amount of [BH<sub>4</sub>]<sup>-</sup> (see supporting information). A *n*-propyl derivative, [Ag<sub>20</sub>{S<sub>2</sub>P(O<sup>i</sup>Pr)<sub>2</sub>]<sub>12</sub>, **3**, can be generated by the latter method. Both **2** and **3** are quite stable in non-polar solvents but decompose in a few hours specifically in chlorinated solvents, whereas nanocluster **2** regenerated into **1**. Both **2** and **3** were structurally characterized by single-crystal X-ray diffraction and their compositions were confirmed by electrospray ionization mass spectrometry (ESI-MS), multinuclear NMR, X-ray photoelectron spectroscopy (XPS), UV/Vis, and EDS for the Ag:S atomic ratio. Furthermore, DFT and TDDFT investigations provide a rationalization of their structure, bonding, stability and optical properties.


The positive ESI-MS spectrum of **2** shows a molecular ion peak at *m/z* 4716.3 (calcd 4716.3), corresponding to the molecular weight of neutral [Ag<sub>20</sub>{S<sub>2</sub>P(O<sup>i</sup>Pr)<sub>2</sub>]<sub>12</sub> (Fig 1a). By analyzing its isotopic pattern, the ionized nanocluster was determined to be mono-charged because the isotope peak spacing is unity (+1) (inset of Fig 1a). Additional peaks in lower and higher mass ranges can be attributed to a fragment [Ag<sub>20</sub>{S<sub>2</sub>P(O<sup>i</sup>Pr)<sub>2</sub>]<sub>11</sub><sup>+</sup> (*m/z* 4503.3) and the adduct [Ag<sub>21</sub>{S<sub>2</sub>P(O<sup>i</sup>Pr)<sub>2</sub>]<sub>12</sub><sup>+</sup> (*m/z* 4823.2), respectively. The UV-vis spectrum of **2** shows broad multiband optical absorption bands (at 260, 360, 435, 443, and 492 nm) and one shoulder band at 540 nm (Fig 1b, S1 and Table S1), whereas the same number of absorption band with shifted positions (at 235, 260, 381, 425, 482 and 540 nm) were also observed in **1**. Both **1** and **2** exhibit luminescence in the near-IR region ~921 nm and ~ 950 nm, respectively. The XPS of **2** shows the existence of both Ag<sup>0</sup> and Ag<sup>I</sup>. The Ag 3d<sub>5/2</sub> XPS peak can be resolved into two peaks at binding energies of 367.63 eV and 368.73 eV (Fig S2), corresponding to Ag<sup>I</sup> and Ag<sup>0</sup>, respectively.<sup>[25]</sup> Further, EDS results of **2** showed Ag and S atomic ratio to be 46.67:53.33 (calc.46.66:53.33) (Fig S3, Table S2).

The crystallization of **2** was performed by vapor diffusion of hexane into a concentrated acetone solution at 4 °C. Rectangular-shaped dark-red crystals of **2**, which crystallize in monoclinic P2<sub>1</sub>/n space group, were obtained in a couple weeks. Fig 2a represents an entire structure of [Ag<sub>20</sub>{S<sub>2</sub>P(O<sup>i</sup>Pr)<sub>2</sub>]<sub>12</sub>. The unit cell consists of

enantiomeric pairs similar to the reported chiral gold nanoclusters ( $\text{Au}_{102}$ ,  $\text{Au}_{38}$  and  $\text{Au}_{28}$ )<sup>[3]</sup> and this is the reason why no optical activity is revealed in its CD spectrum.<sup>[8]</sup> It has an idealized  $C_3$  symmetry with the 3-fold axis passing through atoms  $\text{Ag}_{20}$ ,  $\text{Ag}_1$  and the center of two  $\text{Ag}_3$  triangles (Fig 2a). The architecture of **2** exhibits an  $\text{Ag}_{20}$  kernel stabilized by twelve dtp ligands. The metal core comprises an Ag-centered  $\text{Ag}_{13}$  icosahedron capped by seven Ag atoms. The icosahedron can be seen as a ring of six silver atoms in a chair form, sandwiched between two staggered  $\text{Ag}_3$  triangular faces along the pseudo  $C_3$  axis (side view in Fig 2b). The capping Ag atoms occupy seven of the twenty triangular faces of the icosahedron, in such a way that one of them ( $\text{Ag}_{14}$ ) lies on the  $C_3$  axis and the remaining six locate around the  $C_3$  axis to form three butterfly groups, where hinges are made by alternative side edges of the  $\text{Ag}_6$  chair (Fig 2c). Alternatively, a view along the pseudo  $C_3$  axis of Figure 2d reveals that three groups of capping Ag atoms represent two almost coplanar triangles in a closed to eclipsed position (staggering angle:  $18.7^\circ$ ) in a 3-fold propeller-like shape. The radial and peripheral Ag-Ag distances within the silver-centered  $\text{Ag}_{13}$  icosahedron are in the range 2.7299(5) - 2.8244(5) Å and 2.8605(5) - 3.0111(5) Å, respectively. These distances are shorter than the Ag-Ag distances (2.9171(5) - 3.0266(5) Å) between  $\text{Ag}_{\text{ico}}$  and capping ( $\mu_3$ -Ag) atoms. The ranges in every type of Ag-Ag distances increase in comparison with the corresponding distances in **1** (2.7542(8)-2.8159(8) Å, 2.8420(9)-2.9980(9) Å and 2.813(5)-2.846(5) Å, respectively), indicating a slight expansion of the  $\text{Ag}_{20}$  metallic core.

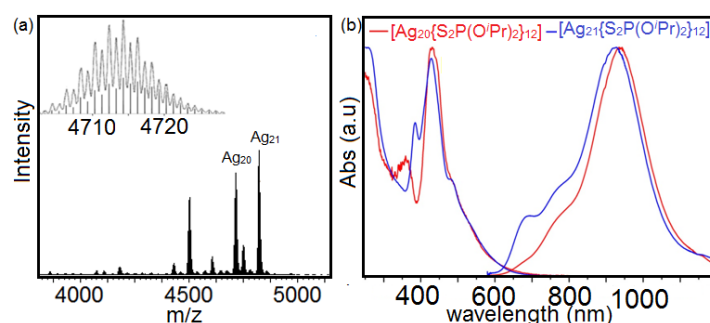


**Figure 1.** (a) ESI-MS spectrum of **2**. The inset shows the experimental (top) and theoretical one (bottom). (b) UV-vis absorption (left-side) and normalized emission (right-side) spectra of **1** and **2** in chloroform.

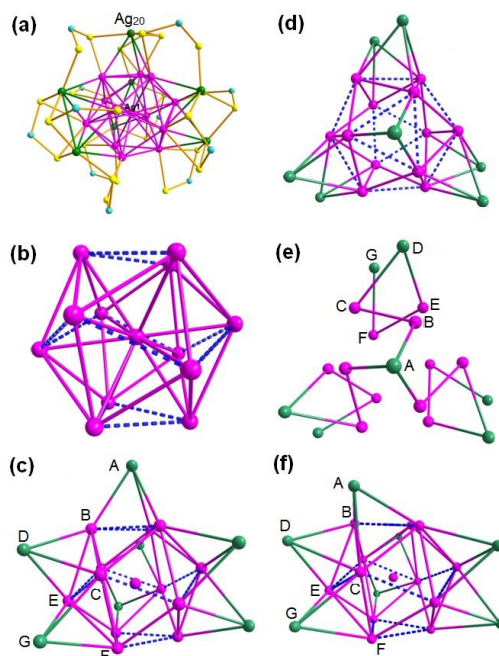

**Figure 2.** (a) Full molecular structure of **2** (isopropoxy groups omitted for clarity). (b) The Ag-centered  $\text{Ag}_{13}$  icosahedron (pink spheres) made of an  $\text{Ag}_6$  ring in a chair form sandwiched between two  $\text{Ag}_3$  triangles in relative staggered conformation (dashed edges in blue). (c) Out of seven capping Ag atoms (green spheres), six are making butterflies around the  $C_3$  axis with hinge positions being alternative edges of the  $\text{Ag}_6$  chair, and labelling of different surface atom types (A-G). (d) A top view of the  $\text{Ag}_{20}$  core, where six capping atoms participate in three-fold propeller. (e) A top views of the three clockwise silver strands constituting the  $\text{Ag}_{20}$  core. (f) The  $\text{Ag}_{20}$  core of **3**, where the capping atom (A), which lies at the  $C_3$  axis in **2** (fig 2c) is now completely off the axis. Ag (pink and green), S (yellow), P (cyan).

The relationship between the molecular structures of **1** and **2** is straightforward. Whereas **1** exhibits an Ag<sub>21</sub> core of idealized D<sub>3</sub> symmetry, one of the two capping silver atoms situated on the three-fold axis is missing in **2**, lowering the symmetry to C<sub>3</sub>, but leaving the remaining cluster topology as a whole basically unchanged. Additionally, there are interactions (3.285 – 3.382 Å) between the capping silver atoms and the wing tips of neighboring butterfly group, which are also observed in **1** and smaller than the sum of Van der Waals radii for silver (3.40 Å).<sup>[26]</sup> A centered icosahedron was also structurally identified in silver nanoclusters stabilized by either thiolated or mixed thiol-phosphine ligand systems such as Ag<sub>25</sub> and Ag<sub>29</sub>,<sup>[15]</sup> whereas an empty Ag<sub>12</sub> icosahedron is present in Ag<sub>44</sub> thiolato-stabilized species.<sup>[14]</sup>

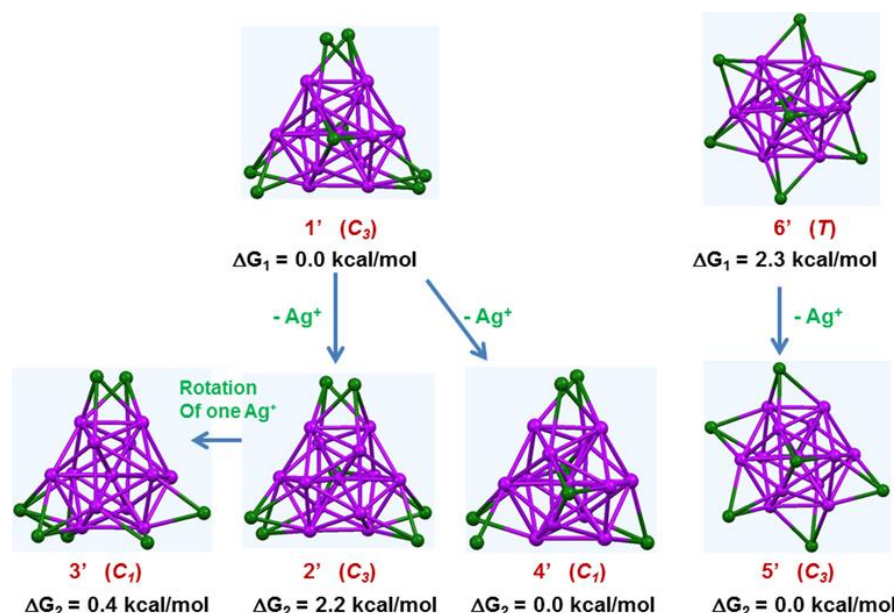

**Figure 3.** Structural relationships of the metallic cores in the [Ag<sub>21</sub>{S<sub>2</sub>PH<sub>2</sub>}<sub>12</sub>]<sup>+</sup> (**1'**, **6'**) and [Ag<sub>20</sub>{S<sub>2</sub>PH<sub>2</sub>}<sub>12</sub>] (**2'**-**5'**) isomers. ΔG<sub>1</sub> and ΔG<sub>2</sub> are the relative free energies at 298 K of the Ag<sub>21</sub> and Ag<sub>20</sub> species, respectively. Ideal symmetries refer to the entire clusters (including the ligands).

The Ag<sub>20</sub> core of **2** represents an unprecedented chiral arrangement of silver atoms as shown in Fig 2c, where the 19 surface Ag atoms can be classified into seven types of symmetry-related atoms (A-G) in a ratio of 1:3:3:3:3:3:3. Three groups of every single Ag atom type create three clockwise helices along the C<sub>3</sub> axis (Fig 2e). *To the best of our knowledge this is the first structural evidence for a silver nanocluster bearing an intrinsic chiral metallic core.* Its structural features are somehow similar to a recently discovered tetradentate phosphine-stabilized gold nanocluster, where an Au<sub>20</sub> core of C<sub>3</sub> symmetry also has an intrinsic chiral inorganic core.<sup>[11]</sup> However in this Au<sub>20</sub> core, the seven capping Au atoms constitute a helical Y-shape over the centered icosahedron Au<sub>13</sub> and its electron count is also different from that of **2**.

The Ag<sub>20</sub> framework in **2** is stabilized by twelve dtp ligands through three spherical rows (top, middle and bottom) in a ratio of 3:6:3 around the pseudo C<sub>3</sub> axis (Fig 2a). The ligands in top and middle spherical rows show trimetallic ( $\eta^3$ ) connectivity with one Ag<sub>ico</sub> and two Ag<sub>cap</sub> atoms via tri ( $\mu_2, \mu_1$ ) and tetra ( $\mu_2, \mu_2$ ) coordination modes, whereas ligands at the bottom row have dimetallic tri-connectivity ( $\eta^2: \mu_2, \mu_1$ ) with one Ag<sub>ico</sub> and one Ag<sub>cap</sub> atoms due to the loss of one capping atom, as compared to **1**. The ligands in middle spherical row have alternatively both trimetallic tetraconnectivity ( $\eta^3: \mu_2, \mu_2$ ) and trimetallic triconnectivity ( $\eta^3: \mu_2, \mu_1$ ) patterns. The bond distances Ag<sub>cap</sub>-S (avg. 2.51 Å) and the S...S bite (avg. 3.401(5)) Å in **2** are identical to their corresponding distances in **1**, but the Ag<sub>ico</sub>-S bond distances are longer (avg. 2.72 Å) in comparison with those of Ag<sub>21</sub> (avg. 2.670 Å).

Among the 19 surface atoms of the Ag<sub>20</sub> core (labeled A-G in Fig 2c), the A-, D- and G-type (Ag<sub>cap</sub>) atoms are bonded to three S atoms in a near trigonal planar conformation, the B-, E- and F-type (Ag<sub>ico</sub>) atoms to two and the C-type (Ag<sub>ico</sub>) atoms to only one. Accordingly, four types of phosphorous ligands are authenticated by the <sup>31</sup>P NMR spectrum of **2** with the appearance of four resonances at 105.21, 104.09, 102.74, 100.33 ppm in an equal integration ratio at -70 °C, whereas only one broad resonance centered at 101.87 ppm was observed at 22 °C (Fig S4a, b). Thus, <sup>31</sup>P NMR study supports the existence of chirality in the nanocluster in solution.

The anatomy of the Ag<sub>20</sub> cores in **3** exhibits a singular difference, as compared to that of **2**. It concerns the location of the capping silver atoms denoted A (Fig 2c, f). Whereas in **2**, AgA lies on the C<sub>3</sub> axis, it is completely off this axis in **3**, in such a way that the idealized C<sub>3</sub> symmetry is now broken (Fig 2f). This effect is likely due to the peculiar steric hindrance of the <sup>n</sup>Pr alkyl groups. *These results indeed provide an important lesson: that is*

atomically precise nanoclusters may have different structures even though their compositions are almost identical.

DFT calculations<sup>[27]</sup> have been carried out at the BP86/Def2-TZVP level on simplified models of formula  $[\text{Ag}_{20}\{\text{S}_2\text{PH}_2\}_{12}]$ . Starting the geometry optimization from the crystal structure of **2** or from the structure of the  $C_3$   $[\text{Ag}_{21}\{\text{S}_2\text{PH}_2\}_{12}]^+$  model<sup>[22]</sup> (**1'**) to which one of the  $\text{Ag}^+$  ions lying on the  $C_3$  axis has been removed, yielded the same energy minimum of nearly  $C_3$  symmetry (**2'**), analogous to the experimental structure of **2** (see Supporting Information). Consistently with its superatom nature, a substantial HOMO-LUMO gap of 1.52 eV is computed for **2'**, which compares well with that of **1'** (1.68 eV). Whereas the optimized Ag-Ag distances in **2'** are, unsurprisingly,<sup>[22c, 23]</sup> somewhat longer than their corresponding experimental counterparts, they follow the same trend. Within the icosahedron they range 2.850 Å – 2.947 Å ( $\text{Ag}_{\text{center}}\text{-Ag}_{\text{ico}}$ ) and 2.942 Å – 3.201 Å ( $\text{Ag}_{\text{ico}}\text{-Ag}_{\text{ico}}$ ). The  $\text{Ag}_{\text{cap}}\text{-Ag}_{\text{ico}}$  distances are as follow:  $\text{Ag}(\text{A})\text{-Ag}_{\text{ico}} = 3.081$  Å,  $\text{Ag}(\text{D})\text{-Ag}_{\text{ico}} = 3.096$  Å (avg.),  $\text{Ag}(\text{D})\text{-Ag}(\text{E}) = 2.956$  Å. In the latter case, the capping atom is found to be in reasonably close contact with only one  $\text{Ag}_{\text{ico}}$  atom (of type E), contrarily to what shows the X-ray structure of **2**. The expansion of the  $\text{Ag}_{20}$  core when going from the experimental to the optimized structure causes the  $\text{Ag}(\text{E})$  atoms to be bonded to only one sulfur atom in **2'**, whereas in **2** they are bonded to two (see above), one of the experimental  $\text{Ag}(\text{E})\text{-S}$  distances being however quite long (2.9369(13) Å). The Wiberg bond indices computed in **2'** follow the structural trends, *i.e.* 0.337 (avg.) and 0.083 (avg.) for the  $\text{Ag}_{\text{center}}\text{-Ag}_{\text{ico}}$  and  $\text{Ag}_{\text{ico}}\text{-Ag}_{\text{ico}}$  bonds, respectively. The  $\text{Ag}_{\text{ico}}\text{-Ag}_{\text{ico}}$  values, averaging 0.032, are significantly lower. As in the case of **1**,<sup>[23]</sup> this is consistent with the view of an icosahedral  $[\text{Ag}_{13}]^{5+}$  superatom system associated with the eight metal electrons in a spherical jellium  $1\text{S}^21\text{P}^6$  configuration,<sup>[24]</sup> surrounded by an  $[\text{Ag}_7(\text{dtp})_{12}]^{5-}$  protecting shell in which the seven  $\text{Ag}_{\text{cap}}$  atoms are in the +I oxidation state, and interact with the icosahedron mainly through metallophilic weak interactions. This view is also supported by the metal computed natural atomic charges (-0.47, +0.24 (avg.) and +0.62 (avg.) for  $\text{Ag}_{\text{center}}$ ,  $\text{Ag}_{\text{ico}}$  and  $\text{Ag}_{\text{cap}}$  respectively. Moreover, it was possible to identify molecular orbitals of **2'** which can be associated with the frontier jellium levels (see Fig S5).

Geometry optimization of the  $[\text{Ag}_{20}\{\text{S}_2\text{PH}_2\}_{12}]$  model starting from the X-ray structure of **3** led to an energy minimum **3'** (HOMO-LUMO gap of 0.52 eV) of similar topology which lies only 1.8 kcal/mol below **2'** (free energy). Its core electronic structure is similar to that of **3'**.

As mentioned above, the structure of **2** (or **2'**) can be derived from that of **1** (or **1'**) by simply removing one of its capping  $\text{Ag}^+$  atoms. However, there are two types of capping atoms in **1** (or **1'**): the two lying on the  $C_3$  axis and the six other ones. Removing one of the latter atoms generates a structure of  $C_1$  symmetry, of different topology from that of **2** (or **2'**) (Fig 3). Optimization of this structure for the  $[\text{Ag}_{20}\{\text{S}_2\text{PH}_2\}_{12}]$  model yielded an isomer **4'** being 2.2 kcal/mol below **2'**. Moreover, another energy minimum, differing from **2'**, **3'** and **4'** by the way the seven capping atoms are distributed around the  $\text{Ag}_{13}$  icosahedron was found. This isomer of  $C_3$  symmetry (**5'**) is computed to be isoenergetic with **4'**. Thus, the four computed isomers lie within a range of 2.2 kcal/mol in free energy, a value hardly significant at our level of modelization. Interestingly, the structure of **5'** can be derived from that of a hypothetical isomer of **1'** of  $T$  symmetry (labeled **6'**), by removing one of its eight symmetry-equivalent capping  $\text{Ag}^+$  atoms. **6'** is computed to be 2.3 kcal/mol above **1'**. The structural relationships of the **1'**-**6'** species are summarized in Fig 3. They all possess the same  $[\text{Ag}_{13}]^{5+}$  superatomic core and similar arrangement of their ligand coverage. They mainly differ by the location of their seven (or eight)  $\text{Ag}^+$  capping atoms. These results suggest that several structural types of  $[\text{Ag}_{20}\{\text{S}_2\text{P}(\text{OR})_2\}_{12}]$  compounds are possible, all with the same superatomic icosahedral  $[\text{Ag}_{13}]^{5+}$  nucleus, but different distribution of their 7  $\text{Ag}^+$  atoms. In the case of isomers, they should exhibit somewhat different optical properties, as exemplified by the TDDFT-simulated UV-vis spectra of **2'**-**5'** shown in Fig S6. The major optical transitions of lowest energy determined for **2'** by TDDFT calculations are found at 459, 484, 532 and 598 nm. They can be assigned to MLCT, LMCT, MMCT and MMCT, respectively. The transition at 598 nm has a rather low oscillating factor and thus is expected of weak intensity. The three other values fit reasonably well with the bands observed for **2** at 435, 443 and 492 nm. The TDDFT-computed CD spectra of the **2'** enantiomers are shown in Fig. S7. The high energy feature at ~ 420 nm is of strong MLCT nature, whereas the low energy one at ~ 625 nm is due to MMCT transitions presenting significant (~ 10-20%)  $\text{Ag}_{\text{center}}/\text{Ag}_{\text{ico}} \rightarrow \text{Ag}_{\text{cap}}$  character.

In summary, new nanoclusters  $[\text{Ag}_{20}\{\text{S}_2\text{P}(\text{OR})_2\}_{12}]$  ( $\text{R} = {}^i\text{Pr}$ ,  ${}^n\text{Pr}$ ) with isomeric, chiral metallic core have been obtained and structurally characterized. The structure of **2** ( $\text{R} = {}^i\text{Pr}$ ) can be derived from that of **1** by simply removing one of the capping atoms lying on the  $C_3$  axis, with only minor additional changes in the overall connectivity and shape of the molecule. This is reminiscent of the structural and chemical relationships between  $[\text{M}_8(\text{H})\{\text{E}_2\text{P}(\text{OR})_2\}_6]^+$  and  $[\text{M}_7(\text{H})\{\text{E}_2\text{P}(\text{OR})_2\}_6]$  ( $\text{M} = \text{Cu}, \text{Ag}; \text{E} = \text{S}, \text{Se}$ ).<sup>[21d]</sup> The structure of cluster **3** ( $\text{R} = {}^n\text{Pr}$ ) can be derived from that of **2** by simply shifting off the capping atom lying on the  $C_3$  axis, generating a chiral structure of  $C_1$  symmetry and revealing structural isomerism in the  $\text{Ag}_{20}$  core. The denticity (tetra vs bidentate) of phosphine and dithiolate ligands used to protect the metallic core plays a key role on the adopted structural distinctions between the intrinsic  $\text{Ag}_{20}$  and  $\text{Au}_{20}$ <sup>[11]</sup> chiral cores. The phenomenon of denticity provides a strong impetus for further work using bidentate ligands to modulate the structures of silver and gold nanoclusters. DFT calculations indicate that the stability of the  $\text{Ag}_{20}$  nanoclusters can be rationalized as that of an 8-electron superatom, composed of an  $[\text{Ag}_{13}]^{5+}$  nucleus stabilized by an  $[\text{Ag}_7\{\text{S}_2\text{P}(\text{OR})_2\}_{12}]^{5-}$  covering shell. Calculations suggest that the shape flexibility of this outer shell can potentially enable to generate low-energy isomers for which different properties might be expected.

## REFERENCES

- [1] a) M.-C. Daniel, D. Astruc, *Chem. Rev.* **2004**, *104*, 293–346; b) R. R. Arvizo, S. Bhattacharyya, R. A. Kudgus, K. Giri, R. Bhattacharya, P. Mukherjee, *Chem. Soc. Rev.* **2012**, *41*, 2943–2970.
- [2] a) J. Sharma, R. Chhabra, A. Cheng, J. Brownell, Y. Liu, H. Yan, *Science*, **2009**, *323*, 112–116; b) C. M. Niemeyer, *Angew. Chem.* **2001**, *113*, 4254–4287; *Angew. Chem. Int. Ed.* **2001**, *40*, 4128–4158; c) M. A. Noginov, G. Zhu, A. M. Belgrave, R. Bakker, V. M. Shalaev, E. E. Narimanov, S. Stout, E. Herz, T. Suteewong, U. Wiesner, *Nature* **2009**, *460*, 1110–1112; d) H. A. Atwater, A. Polman, *Nature Mater.* **2010**, *9*, 205–213.
- [3] R. Jin, *Nanoscale*, **2015**, *7*, 1549–1565.
- [4] P. D. Jadzinsky, G. Calero, C. J. Ackerson, D. A. Bushnell, R. D. Kornberg, *Science* **2007**, *318*, 430–433.
- [5] a) C. Zeng, Y. Chen, K. Kirschbaum, K. Appavoo, M. Y. Sfeir, R. Jin, *Sci. Adv.* **2015**, *1*, e1500045; b) A. Dass, S. Theivendran, P. R. Nimmala, C. Kumara, V. R. Jupally, A. Fortunelli, L. Sementa, G. Barcaro, X. Zuo, B. C. Noll, *J. Am. Chem. Soc.* **2015**, *137*, 4610–4613.
- [6] H. Qian, W. T. Eckenhoff, Y. Zhu, T. Pintauer, R. Jin, *J. Am. Chem. Soc.* **2010**, *132*, 8280–8281.
- [7] C. Zeng, H. Qian, T. Li, G. Li, N. L. Rosi, B. Yoon, R. N. Barnett, R. L. Whetten, U. Landman, R. Jin, *Angew. Chem.* **2012**, *124*, 13291–13295; *Angew. Chem. Int. Ed.* **2012**, *51*, 13114–13118.
- [8] D. Crasto, S. Malola, G. Brosofsky, A. Dass, H. Häkkinen, *J. Am. Chem. Soc.* **2014**, *136*, 5000–5005.
- [9] C. Zeng, T. Li, A. Das, N. L. Rosi, R. Jin, *J. Am. Chem. Soc.* **2013**, *135*, 10011–10013.
- [10] a) M. W. Heaven, A. Dass, P. S. White, K. M. Holt, R. W. Murray, *J. Am. Chem. Soc.* **2008**, *130*, 3754–3755; b) M. Zhu, C. M. Aikens, F. J. Hollander, G. C. Schatz, R. Jin, *J. Am. Chem. Soc.* **2008**, *130*, 5883–5885; c) J. Akola, M. Walter, R. L. Whetten, H. Häkkinen, H. Gronbeck, *J. Am. Chem. Soc.* **2008**, *130*, 3756–3757.
- [11] X.-K. Wan, S.-F. Yuan, Z.-W. Lin, Q.-M. Wang, *Angew. Chem. Int. Ed.* **2014**, *53*, 2923–2926; *Angew. Chem.* **2014**, *126*, 2967–2970.
- [12] Y. Chen, C. Liu, Q. Tang, C. Zeng, T. Higaki, A. Das, D.-E. Jiang, N. L. Rosi, R. Jin, *J. Am. Chem. Soc.* **2016**, *138*, 1482–1485.
- [13] a) C. Sieber, J. Buttet, W. Harbich, C. Félix, R. Mitrić, V. Bonačić-Koutecký, *Phys. Rev. A* **2004**, *70*, 41201–41204; b) H. Dhillon, R. Fournier, *Comp. Theor. Chem.* **2013**, *1021*, 26–34; c) R. Fournier, *J. Chem. Phys.*, **2001**, *115*, 2165–2177; d) E. M. Fernández, J. M. Soler, I. L. Garzón, L. C. Balbá, *Int. J. Quant. Chem.* **2005**, *101*, 740–745.
- [14] a) A. Desireddy, B. C. Conn, J. Guo, B. Yoon, R. N. Barnett, B. M. Monahan, K. Kirschbaum, W. P. Griffith, R. L. Whetten, U. Landman, T. P. Bigioni, *Nature*, **2013**, *501*, 399–402; b) H. Yang, Y. Wang, H. Huang, L. Gell, L. Lehtovaara, S. Malola, H. Häkkinen, and N. Zheng, *Nature Commun.* **2013**, DOI: 10.1038/ncomms3422; c) L. G. AbdulHalim, N. Kothalawala, L. Sinatra, A. Dass, O. M. Bakr, *J. Am. Chem. Soc.* **2014**, *136*, 15865–15868.
- [15] a) C. P. Joshi, M. S. Bootharaju, M. J. Alhilaly, O. M. Bakr, *J. Am. Chem. Soc.* **2015**, *137*, 11578–11581; b) L. G. AbdulHalim, M. S. Bootharaju, Q. Tang, S. d. Gobbo, R. G. AbdulHalim, M. Eddaoudi, D.-E. Jiang, O. M. Bakr, *J. Am. Chem. Soc.* **2015**, *137*, 11970–11975.
- [16] J. Y. Haifeng, H. Su, H. Yang, S. Malola, S. Lin, H. Häkkinen, N. Zheng, *J. Am. Chem. Soc.* **2015**, *137*, 11880–11883.
- [17] M. S. Bootharaju, C. P. Joshi, M. R. Parida, O. F. Mohammed, O. M. Bakr, *Angew. Chem. Int. Ed.* **2016**, *55*, 922–926; *Angew. Chem.* **2016**, *128*, 934–938.
- [18] K. R. Krishnadas, A. Ghosh, A. Baksi, I. Chakraborty, G. Natarajan, T. Pradeep, *J. Am. Chem. Soc.* **2016**, *138*, 140–148.
- [19] N. Cathcart, P. Mistry, C. Makra, B. Pietrobon, N. Coombs, M. Jelokhani-Niaraki, V. Kitaev, *Langmuir* **2009**, *25*, 5840–5846.
- [20] a) V. J. Kitaev, *J. Mater. Chem.* **2008**, *18*, 4745–4749; b) M. Farrag, M. Tschurl, U. Heiz, *Chem. Mater.* **2013**, *25*, 862–870.
- [21] a) R. S. Dhayal, J.-H. Liao, Y.-R. Lin, P.-K. Liao, S. Kahlal, J.-Y. Saillard, C. W. Liu, *J. Am. Chem. Soc.* **2013**, *135*, 4704–4707; b) J.-H. Liao, R. S. Dhayal, X. Wang, S. Kahlal, J.-Y. Saillard, C. W. Liu, *Inorg. Chem.* **2014**, *53*, 11140–11145; c) A. J. Edwards, R. S. Dhayal, P.-K. Liao, J.-H. Liao, M.-H. Chiang, R. O. Piltz, S. Kahlal, J.-Y. Saillard, C. W. Liu, *Angew. Chem. Int. Ed.* **2014**, *53*, 7214–7218; *Angew. Chem.* **2014**, *126*, 7342–7346; d) R. S. Dhayal, J.-H. Liao, S. Kahlal, X. Wang, Y.-C. Liu, M.-H. Chiang, W. E. van Zyl, J.-Y. Saillard, C. W. Liu, *Chem. Eur. J.* **2015**, *21*, 8369–8374; e) R. S. Dhayal, J.-H. Liao, X. Wang, Y.-C. Liu, M.-H. Chiang, S. Kahlal, J.-Y. Saillard, C. W. Liu, *Angew. Chem. Int. Ed.* **2015**, *54*, 13604–13608; *Angew. Chem.* **2015**, *127*, 13808–13812; f) R. S. Dhayal, W. E. van Zyl, C. W. Liu, *Acc. Chem. Res.* **2016**, *49*, 86–95; g) P. V. V. N. Kishore, J.-H. Liao, H.-N. Hou, Y.-R. Lin, C. W. Liu, *Inorg. Chem.* **2016**, *55*, 3663–3673.
- [22] a) C. W. Liu, H.-W. Chang, B. Sarkar, J.-Y. Saillard, S. Kahlal, Y.-Y. Wu, *Inorg. Chem.* **2010**, *49*, 468–475; b) C. W. Liu, H.-W. Chang, C.-S. Fang, B. Sarkar, J.-C. Wang, *Chem. Commun.* **2010**, *46*, 4571–4573; c) C. W. Liu, P.-K. Liaw, C.-S. Fang, J.-Y. Saillard, S. Kahlal, J.-C. Wang, *Chem. Commun.* **2011**, *47*, 5831–5833; d) C. W. Liu, Y.-R. Lin, C.-S. Fang, C. Latouche, S. Kahlal, J.-Y. Saillard, *Inorg. Chem.* **2013**, *52*, 2070–2077; e) C. Latouche, S. Kahlal, Y.-R. Lin, J.-H. Liao, E. Furet, C. W. Liu, J.-Y. Saillard, *Inorg. Chem.* **2013**, *52*, 13253–13262; f) C. Latouche, S. Kahlal, E. Furet, P.-K. Liao, Y.-R. Lin, C.-S. Fang, J. Cuny, C. W. Liu, J.-Y. Saillard, *Inorg. Chem.* **2013**, *52*, 7752–7765; g) C. Latouche, C. W. Liu, J.-

- Y. Saillard, *J. Clust. Sci.* **2014**, *25*, 147–171; h) J.-H. Liao, H.-W. Chang, Y.-J. Li, C.-S. Fang, B. Sarkar, W. E. van Zyl, C. W. Liu, *Dalton Trans.* **2014**, *43*, 12380–12389.
- [23] R. S. Dhayal, J.-H. Liao, Y.-C. Liu, M.-H. Chiang, S. Kahlal, J.-Y. Saillard, C. W. Liu, *Angew. Chem. Int. Ed.* **2015**, *54*, 3702–3706; *Angew. Chem.* **2015**, *127*, 3773–3777.
- [24] a) M. Walter, J. Akola, O. Lopez-Acevedo, P. D. Jadzinsky, G. Calero, C. J. Ackerson, R. L. Whetten, H. Gronbeck, H. Hakkinen, *Proc. Natl. Acad. Sci. USA* **2008**, *105*, 9157–9162; b) H. Häkkinen, *Chem. Soc. Rev.* **2008**, *37*, 1847–1859; c) B. S. Gutrath, I. B. Opper, O. Presly, I. Beljakov, V. Meded, W. Wenzel, U. Simon, *Angew. Chem.* **2013**, *125*, 3614–3617; *Angew. Chem. Int. Ed.* **2013**, *52*, 3529–3532.
- [25] D. Sun, G.-G. Luo, N. Zhang, R.-B. Huang, L.-S. Zheng, *Chem. Commun.* **2011**, *47*, 1461–1463.
- [26] A. Bondi, *J. Phys. Chem.* **1964**, *68*, 441–451.
- [27] Details of the calculations are provided in the Supporting Information.
-