



**HAL**  
open science

## Ultralow Lattice Thermal Conductivity and Enhanced Thermoelectric Performance in SnTe:Ga Materials

Rabih Al Rahal Al Orabi, Junphil Hwang, Chan-Chieh Lin, Regis Gautier, Bruno Fontaine, Woochul Kim, Jong-Soo Rhyee, Daehyun Wee, Marco Fornari

► **To cite this version:**

Rabih Al Rahal Al Orabi, Junphil Hwang, Chan-Chieh Lin, Regis Gautier, Bruno Fontaine, et al.. Ultralow Lattice Thermal Conductivity and Enhanced Thermoelectric Performance in SnTe:Ga Materials. *Chemistry of Materials*, 2017, 29 (2), pp.612–620. 10.1021/acs.chemmater.6b04076 . hal-01500409

**HAL Id: hal-01500409**

**<https://univ-rennes.hal.science/hal-01500409>**

Submitted on 22 May 2017

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Ultra-low Lattice Thermal Conductivity and Enhanced Thermoelectric Performance in SnTe:Ga Materials

Rabih Al Rahal Al Orabi,<sup>\*,†,‡</sup> Junphil Hwang,<sup>¶</sup> Chan-Chieh Lin,<sup>§</sup> Régis Gautier,<sup>||</sup>  
Bruno Fontaine,<sup>||</sup> Woochul Kim,<sup>¶</sup> Jong-Soo Rhyee,<sup>§</sup> Daehyun Wee,<sup>†</sup> and Marco  
Fornari<sup>\*,⊥</sup>

*Department of Environmental Science and Engineering, Ewha Womans University, Seoul,  
120-750, Korea, Department of Physics, Central Michigan University, Mt. Pleasant, MI  
48859, USA, School of Mechanical Engineering, Yonsei University, Seoul, 120-749, Korea,  
Department of Applied Physics, College of Applied Science, Kyung Hee University,  
Yongin-si, Giheung-gi, Gyeonggi-do 446-701, Korea, Institut des Sciences Chimiques de  
Rennes, UMR 6226 CNRS-Université de Rennes 1-Ecole Nationale Supérieure de Chimie  
de Rennes, 11 allé de Beaulieu, CS 50837, F-35708 Rennes, France., and Department of  
Physics and Science of Advanced Materials Program, Central Michigan University, Mt.  
Pleasant, MI 48859, USA*

E-mail: [alrah1r@cmich.edu](mailto:alrah1r@cmich.edu); [marco.fornari@cmich.edu](mailto:marco.fornari@cmich.edu)

---

\*To whom correspondence should be addressed

<sup>†</sup>Department of Environmental Science and Engineering, Ewha Womans University, Seoul, 120-750, Korea

<sup>‡</sup>Department of Physics, Central Michigan University, Mt. Pleasant, MI 48859, USA

<sup>¶</sup>School of Mechanical Engineering, Yonsei University, Seoul, 120-749, Korea

<sup>§</sup>Department of Applied Physics, College of Applied Science, Kyung Hee University, Yongin-si, Giheung-gi, Gyeonggi-do 446-701, Korea

<sup>||</sup>Institut des Sciences Chimiques de Rennes, UMR 6226 CNRS-Université de Rennes 1-Ecole Nationale Supérieure de Chimie de Rennes, 11 allé de Beaulieu, CS 50837, F-35708 Rennes, France.

<sup>⊥</sup>Department of Physics and Science of Advanced Materials Program, Central Michigan University, Mt.

## Abstract

Ultra-low thermal conductivity is of great interest in a variety of field including thermoelectric energy conversion. We report, for the first time, experimental evidence that Ga-doping in SnTe may lower the lattice thermal conduction slightly below the theoretical amorphous minimum at high temperature. Such an effect is justified by the spontaneous formation of nano-precipitates we characterized as GaTe. Remarkably, the introduction of Ga (2-10%) in SnTe also improves the electronic transport properties by activating several hole pockets in the multi-valley valence band. Experimental results are supported with density functional theory calculations. The thermoelectric figure of merit,  $ZT$ , reaches  $\sim 1$  at 873 K in  $\text{Sn}_{0.96}\text{Ga}_{0.07}\text{Te}$ , which corresponds to a  $\sim 80\%$  improvement with respect to pure SnTe.

## Introduction

The thermoelectric effect refers to the direct conversion of a temperature gradient into electrical current or, conversely, the generation of a heat flux by applying an electric field.<sup>1-4</sup> This solid-state technology has a long history of powering spacecrafts in deep space missions and is now being actively developed for waste heat recovery in automotive systems and industrial plants. The performance of a thermoelectric material is described by the dimensionless thermoelectric figure of merit,  $ZT = S^2\sigma T / (k_e + k_l)$ , where  $S$ ,  $\sigma$ , and  $k_e + k_l$  stand for the Seebeck coefficient, the electrical conductivity, and the electronic ( $k_e$ ) and lattice ( $k_l$ ) components of the thermal conductivity.  $T$  is the temperature at which the device is operating. Two main approaches have been used to enhance  $ZT$  and improve the efficiency of energy conversion: (1) the optimization of the power factor,  $S^2\sigma$ , by engineering the electronic properties<sup>5-9</sup> and/or (2) the minimization of  $k_l$  via alloying, tuning of the bond anharmonicities, and nanostructuring.<sup>8,10-22</sup> These approaches lead to a figure of merit  $ZT$  in excess of 2 in lead chalcogenides,  $\text{PbQ}$  ( $\text{Q} = \text{S}, \text{Se}, \text{Te}$ ).<sup>23-30</sup>

---

Pleasant, MI 48859, USA

1  
2  
3  
4 Recently, tin based chalcogenides have been proposed as alternative to PbQ in thermo-  
5 electric power generation because they do not raise environmental concerns associated with  
6 Pb toxicity.<sup>5-9,31,32</sup> Among tin chalcogenides only SnTe adopts the same rock salt structure  
7 as PbQ but it exhibits  $ZT \sim 0.40$  at 900 K.<sup>33</sup> The low value of  $ZT$  was attributed to a high  
8 carrier concentration ( $10^{20} - 10^{21} \text{ cm}^{-3}$ ) caused by intrinsic Sn vacancies combined with a  
9 large separation in energy between valence bands with heavy and light effective masses<sup>34,35</sup>  
10 which limits the Seebeck coefficient. In addition, the small energy band gap ( $\sim 0.18 \text{ eV}$ )<sup>36,37</sup>  
11 is favoring bipolar transport. The limitations of pure SnTe were overcome either by creating  
12 resonant states in the electronic density of states or by controlling the energy of the hole  
13 pockets at the top of the valence band.<sup>5-7,9,38-41</sup>

14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24 The experimental thermal conductivity of pristine SnTe is  $\sim 2.88 \text{ Wm}^{-1}\text{K}^{-1}$  at room tem-  
25 perature.<sup>38</sup> For good thermoelectric performances, values just above the theoretical amor-  
26 phous limit (for SnTe,  $k_{min}$  is equal to  $0.5 \text{ Wm}^{-1}\text{K}^{-1}$ )<sup>6</sup> are required. Recently,  $k_l$  has been  
27 successfully reduced via vacancy scattering,<sup>42</sup> alloying formation or/and the introduction of  
28 the second phase nano-precipitates in few SnTe based materials,<sup>5,6,38,42-46,46</sup> however, to the  
29 best of our knowledge, the amorphous limit was never reached. Here, we report for the first  
30 time the reduction of  $k_l$  to  $\sim 0.455 \text{ Wm}^{-1}\text{K}^{-1}$  at  $T \geq 776 \text{ K}$  for Ga-doped SnTe, slightly  
31 below the theoretical  $k_{min}$  for SnTe.<sup>6</sup>

32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
Ga doping has been well investigated in *n*-type PbSe and significantly improved of the  
power factors compared to those of pristine PbSe. The similarities in band and crystal struc-  
tures between PbSe and SnTe hinted that Ga-doping could favorably modify the electronic  
properties.<sup>47</sup> Zhao et al.<sup>44</sup> recently suggested the substitution of a small amounts (3%) of  
Sn with Ga decreases the lattice thermal conductivity from  $3.2 \text{ Wm}^{-1}\text{K}^{-1}$  to  $2 \text{ Wm}^{-1}\text{K}^{-1}$   
at room temperature in SnTe. We were able to increase the Ga content in SnTe up to 10%  
and exploit the increased disorder to reach  $k_{min}$ . In addition, we show that Ga doping in  
SnTe improves the electronic properties by activating several hole pockets with larger ef-  
fective masses, resulting in an enhanced Seebeck coefficient and power factor. Overall, an

1  
2  
3 optimized thermoelectric figure of merit  $ZT$  of 0.99 has been achieved at 873 K for 7% Ga-  
4 doped SnTe sample, which make the heavily doped  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  system attractive for the  
5 mid-temperature thermoelectric power generation.  
6  
7  
8  
9

## 10 11 12 **Experimental procedures**

### 13 14 15 **Samples preparation**

16  
17 Recently, Tan et al.<sup>38</sup> have shown that Sn self-compensation is an effective path for enhancing  
18 the thermoelectric performance of SnTe by decreasing the hole carrier density. High quality  
19 ingots with nominal compositions of  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  ( $x = 0, 0.02, 0.03, 0.05, 0.07$  and  $0.1$ )  
20 were synthesized by mixing appropriate ratios of high purity elemental precursors from Sn  
21 shot (99.999+ %), Ga shot (99.5+ %) and Te shot (99.999+ %) in silica tubes. The tubes  
22 were then evacuated to a residual pressure of  $\sim 10^{-4}$  Torr, flame sealed and slowly heated  
23 to 1023 K, soaked at this temperature for 3 h, then heated up to 1273 K in 3 h, soaked for  
24 10 h to ensure the homogeneity of composition and subsequently quenched in ice water.  
25  
26  
27  
28  
29  
30  
31  
32  
33

34  
35 The obtained samples of  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  were ground into fine powders and then densified  
36 by sintering (at  $\sim 10^{-2}$  mbar) via hot uniaxial pressing (HUP). The pressing conditions were  
37 as follows: the pressure was applied from the beginning of the temperature ramp to the end  
38 of the high-temperature dwell. A typical quantity of 10 g of powder was introduced into 12  
39 mm diameter graphite dies previously coated with boron nitride. The applied load was 50  
40 MPa at 800 K for 2 h for all experiments. The densities for all pellets were calculated to be  
41 95% of the theoretical values after measuring volume and weight.  
42  
43  
44  
45  
46  
47  
48  
49  
50

### 51 52 **Powder X-ray diffraction and scanning electron microscopy**

53  
54 Samples were characterized by powder X-ray diffraction (PXRD) with Cu  $K_\alpha$  ( $\lambda = 1.5406$   
55 Å) radiation at room temperature using a Bruker D8 diffractometer. Lattice constants  
56 and volumes were calculated by Rietveld refinement using the Fullprof software. Scanning  
57  
58  
59  
60

1  
2  
3 electron microscopy energy dispersive spectroscopy (EDS) imaging were carried out using a  
4 JSM-6701F microscope.  
5  
6  
7

## 8 9 **Electrical transport measurements**

10 The HUPed pellets were cut into  $\sim 3.5$  mm x 3.5 mm x 10 mm bars for simultaneous  
11 measurement of the electrical conductivity and the Seebeck coefficient. Measurements were  
12 performed under He atmosphere from room temperature to 873 K using a Ulvac Riko ZEM-3  
13 instrument. The room temperature Hall coefficients were measured using a PPMS system.  
14 Four-contact Hall-bar geometry was used for the measurement. The effective carrier con-  
15 centration ( $N_p$ ) was estimated using the relationship  $N_p = 1/eR_H$ , where  $e$  is the electronic  
16 charge and  $R_H$  is the Hall coefficient. The Hall mobility ( $\mu_H$ ) was calculated using the  
17 relationship  $\mu_H = \sigma R_H$  with  $\sigma$  being the electrical conductivity.  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29

## 30 **Thermal transport measurements**

31 The HUPed pellets were cut and polished into a squared-shaped of  $\sim 10$  mm x 10 mm x  
32 1 mm and cylinder-shaped of  $\sim 12$  mm in diameter and 1 mm thick for thermal diffusivity  
33 measurements. The thermal diffusivity coefficient ( $D$ ) was measured with a laser flash dif-  
34 fusivity method using apparatus (Netzsch LFA 457). The heat capacity ( $C_p$ ) was obtained  
35 by  $C_p = C_{p,300} + C_{p1} \times ((T/300)^\alpha - 1)/((T/300)^\alpha + C_{p1}/C_{p,300})$ ,<sup>48</sup> where  $T$  is the absolute  
36 temperature and  $C_{p,300}$  is the specific heat capacity at 300 K. For  $\text{Sn}_{1.03}\text{Te}$ ,  $C_{p,300}$  is 0.1973  
37  $\text{Jg}^{-1}\text{K}^{-1}$ ,  $C_{p1}$  is 0.0531  $\text{Jg}^{-1}\text{K}^{-1}$  (calculated using the specific heat measurement for  $\text{Sn}_{1.03}\text{Te}$   
38 previously reported by Tan et al.<sup>46</sup>). The parameter  $\alpha$  is 0.63. The total thermal conduc-  
39 tivity,  $k$ , was calculated using the formula  $k = DC_p d$  where  $d$  represents the density of the  
40 sample. The uncertainty of the thermal conductivity was estimated to be within 8%, consid-  
41 ering the uncertainties from  $D$ ,  $C_p$ , and  $d$ . The combined uncertainty for all measurements  
42 involved in the calculation of  $ZT$  is less than 15%.  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

# Computational procedures

## First principles calculations

Our calculations are based on density functional theory (DFT). We used the full-potential linearized augmented plane wave (FLAPW) approach, as implemented in the WIEN2K code.<sup>49</sup> The muffin-tin radii ( $R_{MT}$ ) were chosen small enough to avoid overlapping during the structural optimization. A plane-wave cutoff corresponding to  $R_{MT}K_{max} = 7$  was used in all calculations. The radial wave functions inside the non-overlapping muffin-tin spheres were expanded up to  $l_{max} = 12$ . Total energy convergence was achieved with respect to the Brillouin zone (BZ) integration mesh with 500  $k$ -points.

Structure relaxations were performed using the PBE functional for the 64-atoms cubic supercells for  $\text{Sn}_{32}\text{Te}_{32}$ , and  $\text{Sn}_{30}\text{Ga}_2\text{Te}_{32}$  ( $\sim 6$  mol % Ga-doped) with Ga atoms substituted for Sn atoms in SnTe. The Ga sublattice was simple cubic for  $\text{Sn}_{32}\text{Te}_{32}$ , body-centered cubic for  $\text{Sn}_{30}\text{Ga}_2\text{Te}_{32}$ . During the geometry optimization, both the atomic positions and lattice constant were fully relaxed until forces acting on all atoms become less than  $0.02$  eV/Å.

For the electronic band structures we used the modified Becke-Johnson (mBJ) functional which leads to excellent agreement with the experimental values for the energy separation between the highest occupied molecular orbital (HOMO) and the lowest unoccupied molecular orbital (LUMO).<sup>50</sup> We represented the band structures along the high symmetry lines of the cubic Brillouin zone (supercell) for direct analysis of the effects of Sn-Ga substitutions. We used 20000  $k$ -points in the BZ to compute the density of states (PDOS).

## Results and discussion

PXRD analysis indicates that, within the detection limit, the  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  samples exhibit single phase rock-salt SnTe structures for Ga concentration below 5% ( $x \leq 0.05$ , Figure 1a). At higher Ga content ( $x > 0.5$ ), secondary phase peaks appear (Figure 1a for  $25^\circ \leq 2\theta \leq 30^\circ$ )

which match with the PXRD pattern of GaTe (Figure 1c). The lattice parameters decrease linearly with the increase of Ga content, consistently with the smaller ionic radius of Ga compared to that of Sn. Vegard's law (Figure 1b) describes well the variation of lattice parameters up to  $x = 0.05$ . Above that concentration the data deviate. Data indicate a uniform solid solution between GaTe and SnTe for  $x \leq 0.05$ . For  $x > 0.05$ , SnTe-GaTe is partly alloyed and partly phase separated. Ga solubility in SnTe (estimated with PXRD) is substantially lower than Ca, Mg and Mn ( $\sim 12$  mol %) and larger than that of Cd and Hg ( $\sim 3$  mol %) <sup>5-7,9,38</sup> doped SnTe. Morphological features at the nanoscale were observed with high resolution SEM as discussed later in this article.

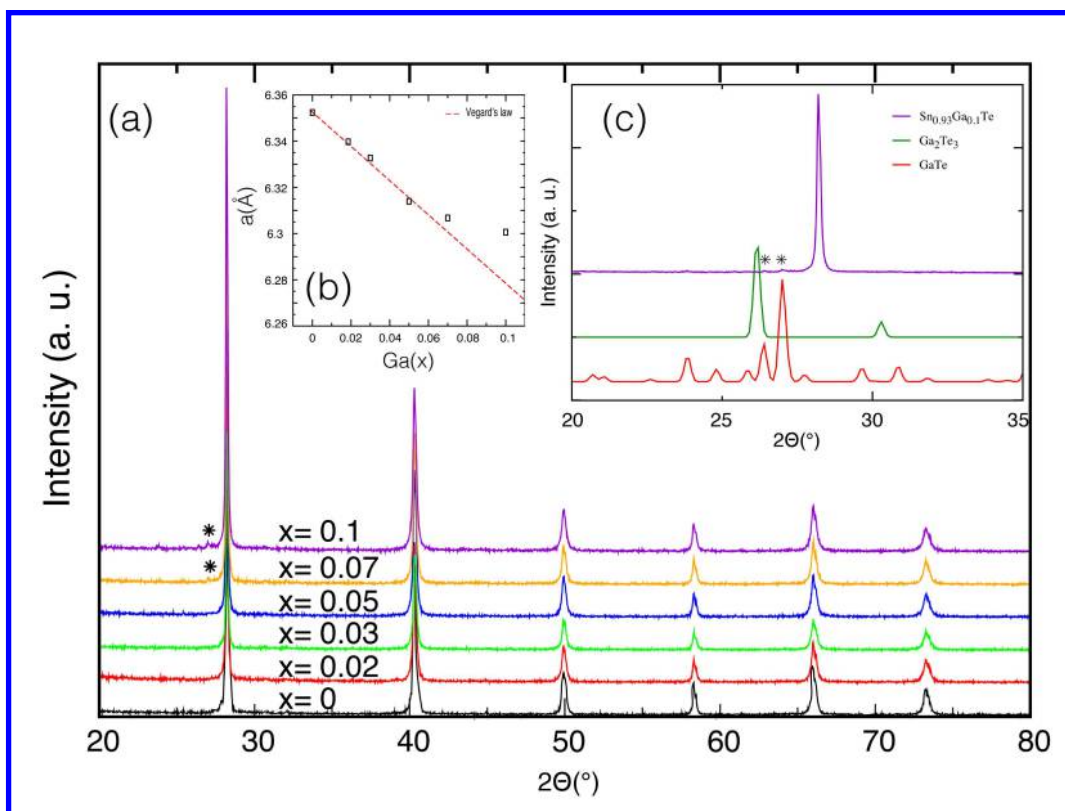


Figure 1: (a) Powder X-ray diffraction patterns of  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  samples ( $x = 0.00, 0.02, 0.03, 0.05, 0.07$  and  $0.1$ ). (b) Lattice parameter as function of Ga concentration; the red dashed line indicates the Vegard's law for the solid solution. (c) Close-up showing the patterns of  $\text{Sn}_{0.93}\text{Ga}_{0.1}\text{Te}$ ,  $\text{GaTe}$ , and  $\text{Ga}_2\text{Te}_3$  compounds.

Figure 2 displays the total ( $k_{tot}$ , panel a) and lattice thermal conductivity ( $k_l$ , panel b) as a function of temperature for  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  samples. The substitution of Ga in



1  
2  
3  
4 SnTe substantially reduces the total thermal conductivity from 8.1  $W/mK$  to 6.2  $W/mK$   
5  
6 at room temperature and from 2.7  $W/mK$  to  $\sim 2.27$   $W/mK$  at 873 K. This reduction in  
7  
8  $k_{tot}$  is attributed to the significant reduction of  $k_l$ . The electrical thermal conductivity  
9  
10 is proportional to the electrical conductivity according to the Wiedemann-Franz relation  
11  
12  $k_e = \sigma LT$ . Here, the Lorenz number,  $L$ , was estimated as a function of temperature from the  
13  
14 experimental Seebeck coefficients using the single parabolic band model and assuming that  
15  
16 acoustic phonon scattering limits the mobility as explained in previous literature (Figure  
17  
18 2d in SI).<sup>51</sup> The lattice thermal conductivity decreases with increasing Ga concentration,  
19  
20 presumably because of the concomitant increase of the alloy disorder and, possibly, the  
21  
22 contribution of interfacial phonon scattering. The samples with 7% and 10% Ga doping  
23  
24 exhibit the lowest lattice thermal conductivity of  $\sim 0.48$   $W/mK$  at 723 K, just below the  
25  
26 theoretical minimum lattice thermal conductivity for SnTe which was estimated using the  
27  
28 model proposed by Cahill et al.<sup>52</sup> The reduction of  $k_l$  is about  $\sim 75\%$  for heavily Ga doped  
29  
30 SnTe samples, reaching values far below  $k_l$  reported previously in In-/Cd-/Mn/Mg and Sb-  
31  
32 doped SnTe (Figure 2d) and comparable only to the values achieved recently in PbTe by  
33  
34 SrTe alloying.<sup>5,6,38,43,44,53,54</sup>

35  
36 The Klemens's model<sup>55,56</sup> of disordered alloys was applied to predict the variation of  
37  
38 the lattice thermal conductivity (at room temperature) of the  $Sn_{1.03-x}Ga_xTe$  samples as  
39  
40 function of the Ga concentration (Figure 2c). The input parameters used for the calculation  
41  
42 are listed on the table 1 (See SI) . For  $x \leq 0.05$ , experimental  $k_l$  values agree well with  
43  
44 the Klemens model, indicating that the point defect scattering caused by Ga alloying is the  
45  
46 dominant factor at small Ga content. However, when  $x > 0.05$ , the experimental  $k_l$  values fall  
47  
48 below the Klemens model, indicating that additional mechanisms associated with nanoscale  
49  
50 precipitates contribute to the phonon scattering.<sup>8,10-14</sup>

51  
52  
53  
54  
55  
56  
57  
58  
59  
60

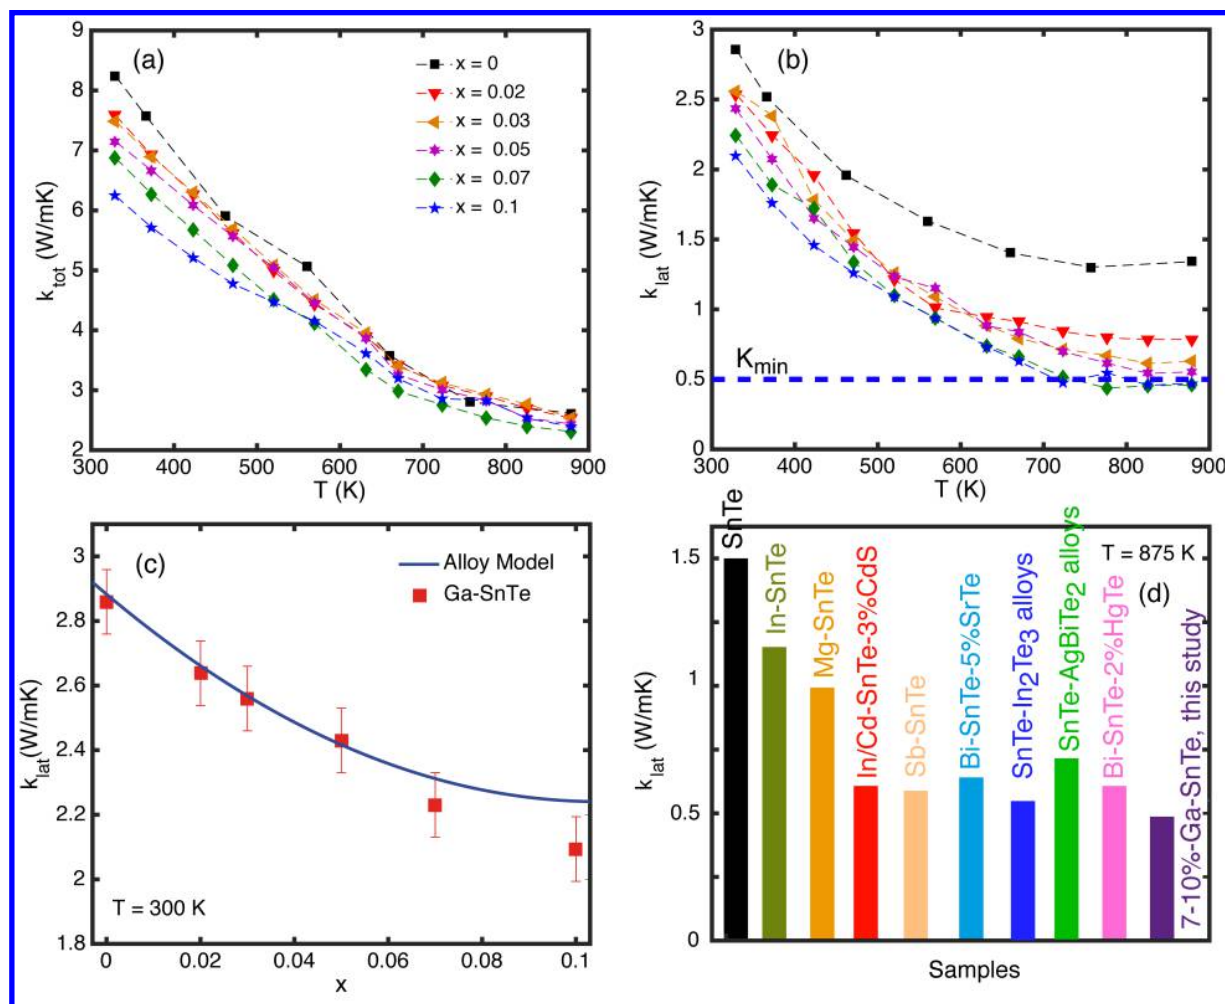


Figure 2: Temperature dependence of (a) total thermal conductivity and (b) lattice thermal conductivity for Sn<sub>1.03-x</sub>Ga<sub>x</sub>Te ( $x = 0, 0.02, 0.03, 0.05, 0.07$  and  $0.1$ ) samples. (c) Room temperature lattice thermal conductivity as function of Ga concentration. Error bars are indicated (10%). The dashed blue line corresponds to the theoretical amorphous limit<sup>57</sup> for Sn<sub>1.03-x</sub>Ga<sub>x</sub>Te.<sup>55,56</sup> (d) Comparison of the high temperature  $k_{\text{lat}}$  of the 7% and 10% Ga-doped SnTe samples with the values reported for In/Mg/In-Cd/Bi-3%SrTe/Bi-2%HgTe doped SnTe,<sup>5,6,38,43-45</sup> and SnTe-In<sub>2</sub>Te<sub>3</sub>, SnTe-AgBiTe<sub>2</sub> alloy materials.<sup>42,46</sup>

In order to explicate the mechanism behind the observed low lattice thermal conductivity in Ga-doped SnTe, we performed the SEM/EDS analysis of pure, 5%, and 10% Ga-doped SnTe (see Figure 3). The SEM images for Sn<sub>1.03</sub>Te and Sn<sub>0.98</sub>Ga<sub>0.05</sub>Te show uniform samples with no obvious nanoscale precipitates in the matrix; this result is consistent with the PXRD results shown in Figure 1 and Figure 1 a,d,f in SI. For 10% Ga doping, we observed numerous nanoscale precipitates (highlighted by the red circles, Figure 3c). The EDS element mapping (Figure 3d) indicates Te, Ga, and Sn distribution respectively pointing to the chemical

composition of precipitates which are rich in Ga, but deficient in Sn. Tellurium distribution is uniform across the sample. We consider this an indication that the inhomogeneities within the matrix effectively decrease the lattice thermal conductivity (Figure 2c) and lead to improved thermoelectric performance.

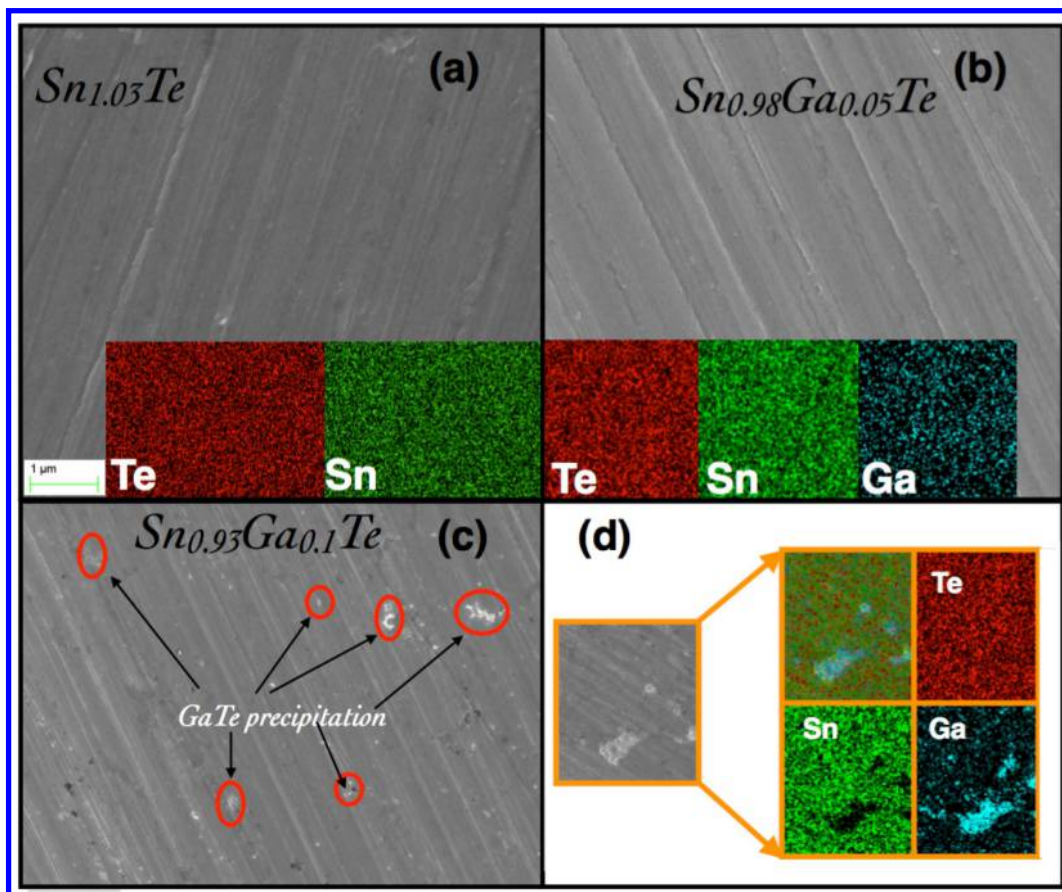


Figure 3: (a) SEM/EDS images of  $\text{Sn}_{1.03}\text{Te}$ , (b)  $\text{Sn}_{0.98}\text{Ga}_{0.05}\text{Te}$ , (c)  $\text{Sn}_{0.93}\text{Ga}_{0.1}\text{Te}$  samples and (d)  $\text{GaTe}$  precipitates in  $\text{Sn}_{0.93}\text{Ga}_{0.1}\text{Te}$  sample, shows the SEM/EDS mapping of Te, Ga, and Sn edges

Figure 4 shows the temperature dependent electrical transport properties of  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  samples. As expected in a degenerate semiconductor, the electrical conductivity,  $\sigma$ , decreases with increasing temperature (Figure 4 a). The presence of Ga introduces scattering phenomena in SnTe leading to a decrease in  $\sigma$  from  $8766 \text{ S cm}^{-1}$  to  $5483 \text{ S cm}^{-1}$  at room temperature, while the electrical conductivities at high temperature for all Ga-doped samples are only slightly smaller than in pure SnTe. Similar trend was found on the Ca, Cd, and Mn

1  
2  
3 doped SnTe.<sup>5-7,9,38</sup>  
4

5 The room temperature carrier concentrations ( $N_p$ ) are shown in Figures 4b. For all  
6 Sn<sub>1.03-x</sub>Ga<sub>x</sub>Te (  $0 \leq x \leq 0.09$ ) samples, the room temperature Hall coefficients,  $R_H$ , are  
7 positive, as expected for  $p$ -type carriers. The  $N_p$  at 300 K increase gradually with increasing  
8 concentration until 7% and then decrease for 10% concentration. Anomalous changes in the  
9 carrier concentration with the increase of Ga concentration are difficult to explain but we  
10 can conjecture that the presence of substitutional defects influences the formation energy of  
11 the vacancies. A similar phenomena was observed recently with In, Mg, Cd, Ca and Hg,  
12 Mn doped in SnTe.<sup>5,6,9,38</sup> The room temperature mobilities ( $\mu_H$ ) of Sn<sub>1.03-x</sub>Ga<sub>x</sub>Te samples  
13 are presented in Figure 4c. We observe a reduction in  $\mu_H$  with increasing Ga doping which  
14 accounts for the reduced electrical conductivity in highly doped samples. The gradual loss  
15 of mobility in SnTe with increasing Ga content may be caused by increased point defect  
16 scattering within solid solution or interfacial scattering caused by GaTe nano-precipitates  
17 for  $x = 7-10\%$ .  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

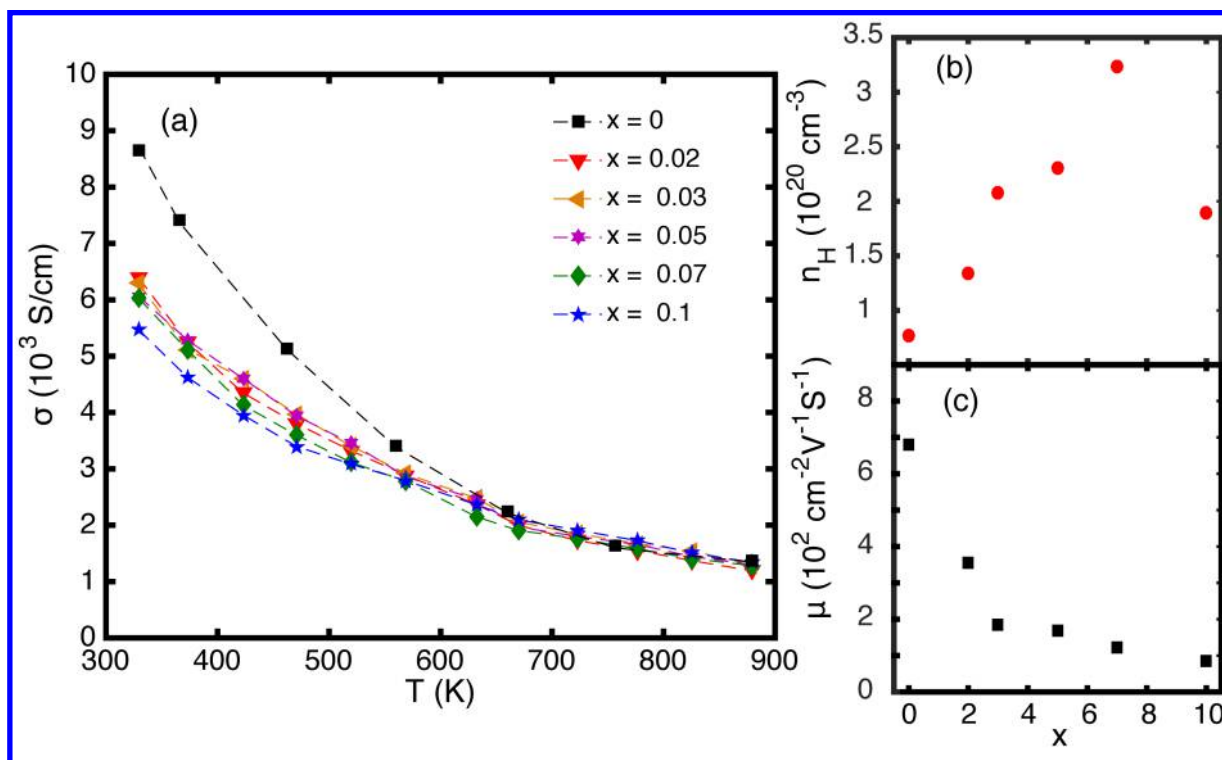


Figure 4: (a) Temperature dependence of electrical conductivity in  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  samples. (b) Carrier concentration ( $N_p$ ) and (c) carrier mobility ( $\mu$ ) at room temperature with respect to Ga alloying concentration ( $x$ ).

We studied also the temperature dependence of the Seebeck coefficient for all our samples (Figure 5a). A positive values of Seebeck coefficient for all samples indicates the  $p$ -type conduction in the temperature range studies of 300-873 K. The Seebeck coefficients are consistent with hole conductivity and increase almost linearly with temperature. As mentioned earlier, the pristine SnTe exhibits a low Seebeck coefficient of  $\sim 15 \mu\text{V}/\text{K}$  at 300 K and reach the maximum value of  $\sim 140 \mu\text{V}/\text{K}$  at 873 K. The introduction of Ga in  $\text{Sn}_{1.03}\text{Te}$  leads to a remarkable enhancement in  $S$  at both low and high temperature: the improvement is up to  $23 \mu\text{V}/\text{K}$  at room temperature and greater than  $40 \mu\text{V}/\text{K}$  at high temperature. The effectiveness of Ga alloying is reflected in the carriers' effective mass ( $m^*$ ) that we derived for each sample using the room temperature  $S$  and  $N_p$ , and considering a single parabolic band model.<sup>51,58</sup> Using the Seebeck coefficient, the chemical potential ( $\mu$ ) can be estimated using eq 1 with ( $\lambda = 0$ , acoustic-phonon scattering), where  $F_j(\mu)$  are the Fermi integrals given in eq 2. The hole effective mass can then be determined from eq 3 using the measured

carrier concentration ( $N_p$ ).

$$S = \frac{k_B}{e} \left\{ \frac{(2 + \lambda)F_{1+\lambda}(\mu)}{(1 + \lambda)F_\lambda(\mu)} - \mu \right\} \quad (1)$$

$$F_j(\mu) = \int_0^\infty \frac{\zeta^j d\zeta}{1 + e^{(\zeta - \mu)}} \quad (2)$$

$$m^* = \frac{h^2}{2k_B T} \left[ \frac{N_p}{4\pi F_{1/2}(\mu)} \right]^{2/3} \quad (3)$$

The  $m^*$  increases gradually from 0.133  $m_e$  to 0.8  $m_e$  ( $m_e$  is the free electron mass) with increasing Ga content from 0 to 10 mol% (Table 1), which is resulting probably due to the increasing contribution of several hole pockets in the multi-valley valence band of SnTe.

Table 1: Carrier concentration ( $N_p$ ) and effective mass ( $m^*$ , in term of the electron mass  $m_e$ ) for  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  ( $x = 0, 0.02, 0.03, 0.05, 0.07$  and  $0.1$ ) samples at 300 K.

Compositions	$N_p$ ( $10^{20}\text{cm}^{-3}$ )	$m^*(m_e)$
$\text{Sn}_{1.03}\text{Te}$	0.77	0.133
$\text{Sn}_{1.01}\text{Ga}_{0.02}\text{Te}$	1.35	0.273
$\text{SnGa}_{0.03}\text{Te}$	2.1	0.44
$\text{Sn}_{0.98}\text{Ga}_{0.05}\text{Te}$	2.4	0.54
$\text{Sn}_{0.96}\text{Ga}_{0.07}\text{Te}$	3.3	0.8
$\text{Sn}_{0.93}\text{Ga}_{0.1}\text{Te}$	1.94	0.62

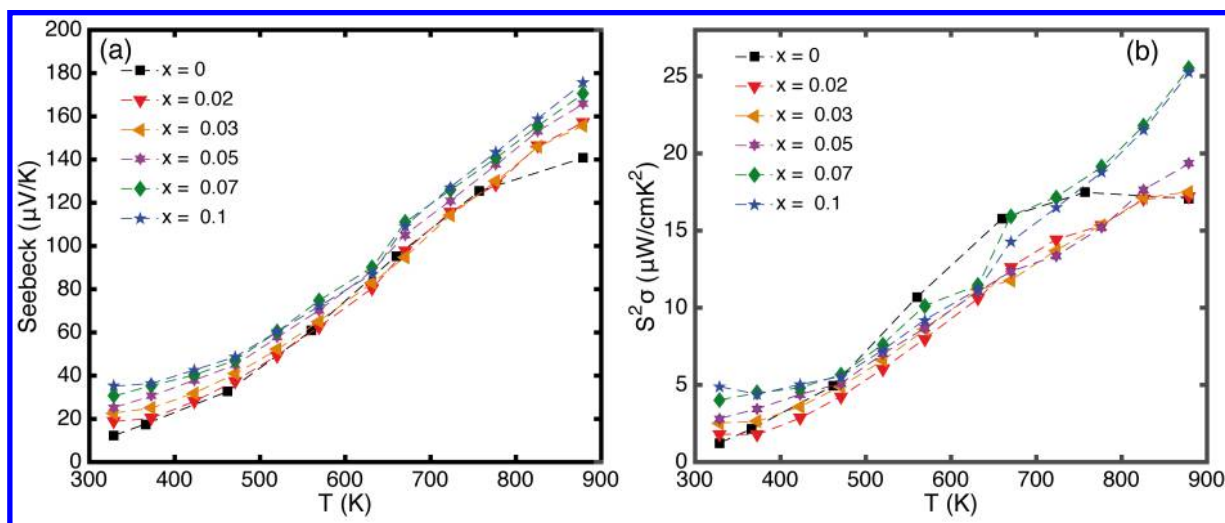


Figure 5: (a) Temperature dependence of Seebeck coefficient ( $S$ ) (b) and power factor ( $S^2\sigma$ ) of  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  ( $x = 0, 0.02, 0.03, 0.05, 0.07$  and  $0.1$ ) samples.

The temperature-dependent power factors of  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  are plotted in (Figure 5b). Due to the enhancement in the Seebeck coefficient at both low and high temperatures, the Ga-doped samples have much higher values than the pure SnTe samples. For instance, the power factor increases from  $2 \mu\text{Wcm}^{-1}\text{K}^{-2}$  to  $5 \mu\text{Wcm}^{-1}\text{K}^{-2}$  at room temperature and from  $16 \text{Wcm}^{-1}\text{K}^{-2}$  to  $26 \text{Wcm}^{-1}\text{K}^{-2}$  at high temperature. The highest power factor obtained is  $26 \text{Wcm}^{-1}\text{K}^{-2}$  at 873 K for  $\text{Sn}_{0.96}\text{Ga}_{0.07}\text{Te}$ . This power factor values achieved with Ga-doped SnTe are comparable to those of PbTe.<sup>12,29,59</sup> Although, the power factors saturate for  $x \geq 0.07$  due to the presence of GaTe second phase (Figure 1a) which deteriorates the carrier mobility, the Seebeck coefficient (Figure 5a) is unaffected.

Aiming to clarify the improved electronic properties, we performed DFT calculations to determine the electronic structure of pristine SnTe and 6% Ga-doped SnTe. It was proved that the band structure of pure SnTe does not favor large thermoelectric performances because of the value of band gap ( $E_g = 0.12 \text{ eV}$ ) below the optimal one predicted by Goldsmid-Sharp formula,<sup>60</sup> low effective masses associated with the dispersive character of valence bands active in transport, and the large offset between the light and heavy holes ( $\Delta E \sim 0.35 \text{ eV}$ ) at 300K. However, upon proper alloying with Ca/Mg/Cd/Mn/Hg/Sb in SnTe, the energy separation,  $\Delta E$ , significantly decreases opening the possibility to improve

1  
2  
3 the thermoelectric properties adding carriers from multiple band extrema with different ef-  
4 fective masses.  
5  
6

7 The projected density of states (PDOS) of  $\text{Sn}_{32}\text{Te}_{32}$  and  $\text{Sn}_{30}\text{Ga}_2\text{Te}_{32}$  supercells are shown  
8 in Figure 6a and b, respectively. Contrary to Ca-, Mg-, Cd-, Mn-, and Hg-doping in SnTe,  
9 Ga-doping does not affect the energy separation between the electronic states at the top  
10 of the valence band (that are empty states after doping) and the electronic states at the  
11 bottom of the conduction band (we obtained  $E_g = 0.12$  eV for SnTe in agreement with  
12 recent experimental data).<sup>5</sup> Ga alloying in SnTe does not seem to create resonant states,  
13 which are characterized by humps in proximity of the Fermi level.<sup>43</sup>  
14  
15  
16  
17  
18  
19  
20  
21

22 As shown in Figures 6c and 3 (SI), the energy gap between valence and conduction  
23 manifolds is direct for all concentrations. Just below the top of the valence band, several  
24 other bands are present and may contribute to the transport properties with appropriate  
25 tuning of  $\Delta E$  and the position of the Fermi level. Since the substitution of Sn by Ga  
26 decreases the number of electrons, the Fermi level moves downward as the amount of Ga  
27 doping increases. The maximum between  $R$  and  $X$  in the BZ (see Figure 6c) is quasi-  
28 degenerate with the pockets in the  $\Gamma$ - $R$  and  $\Gamma$ - $X$  directions. Interestingly, we found that  
29 such a maximum occurs away from the symmetry line greatly increasing the number of  
30 degenerate valleys that contribute to the electronic transport.  
31  
32  
33  
34  
35  
36  
37  
38  
39

40 In order to assess the performance with respect to other compositions, we compiled  
41 data available from the literature<sup>5,6,33,38,43,61,62</sup> with our results using  $S$  vs.  $N_p$  plot for  
42  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  samples (we used room temperature data) and compared with the theoretical  
43 curve (Pisarenko plot) obtained within a simple valence band model by Zhang et al.<sup>43</sup> This  
44 model used a light-hole band effective mass of  $0.168m_e$ , a heavy-hole band effective mass of  
45  $1.92m_e$ , and an energy gap between the two valence band maxima of 0.35 eV. The data for  
46 Cu, Sb and Bi doped and un-doped SnTe samples fall exactly on the Pisarenko curve, while  
47 the In, Ca/Cd/Hg/Mg alloyed SnTe samples show much higher Seebeck coefficient than the  
48 theoretical curve due to the formation of resonance levels,<sup>43</sup> and/or an optimized multi-  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



valley band structure near the Fermi level.<sup>5,6,38</sup> Our Ga-doped SnTe samples also display larger Seebeck coefficients than the Pisarenko curve.

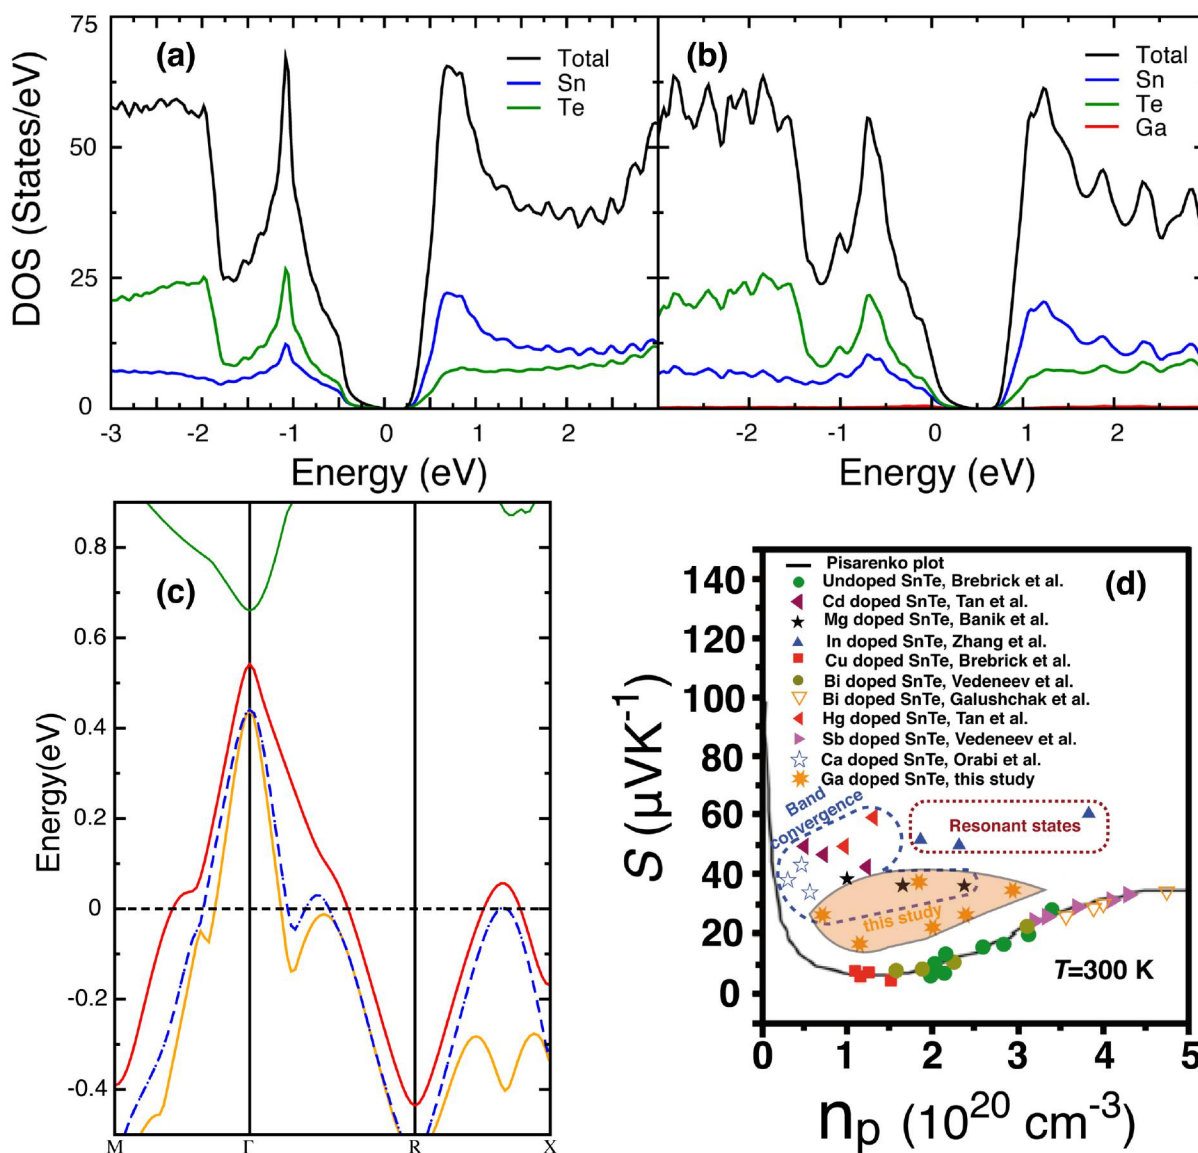


Figure 6: Density of states calculations of (a) undoped SnTe ( $\text{Sn}_{32}\text{Te}_{32}$ ), (b)  $x \sim 6\%$  Ga-doped SnTe ( $\text{Sn}_{30}\text{Ga}_2\text{Te}_{32}$ ). (c) Electronic band structure calculations of  $\sim 6\%$  Ga-doped SnTe ( $\text{Sn}_{30}\text{Ga}_2\text{Te}_{32}$ ) cubic supercell computed from DFT and (d) room temperature  $S$  vs.  $N_p$  plot. Data are from this work for  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  and from previously reported experiments for pure SnTe,<sup>61</sup> and Cd-,<sup>38</sup> Mg-,<sup>5</sup> In-,<sup>43</sup> Cu-,<sup>62</sup> Bi-,<sup>33</sup> Hg-,<sup>6</sup> Sb-,<sup>33</sup> Ca-doping.<sup>9</sup> The theoretical Pisarenko curve is also plotted.<sup>43</sup>

The overall thermoelectric performances are shown in Figure 7a where we plot the temperature dependent figure of merit,  $ZT$ , for all our samples. Benefiting from the great reduction of lattice thermal conductivity and enhanced power factor,  $ZT$  in SnTe is greatly

enhanced by Ga doping, with the highest value reaching  $\sim 1$  at 873 K in  $\text{Sn}_{0.96}\text{Ga}_{0.07}\text{Te}$ . This value is  $\sim 80\%$  improved with respect to  $\text{Sn}_{1.03}\text{Te}$  and higher to previously reported maximum  $ZT$  with Cd/Bi/Sb and In singly doped SnTe (Figure 7b), and also outperforms other  $p$ -type lead-free thermoelectric materials (Figure 7c).

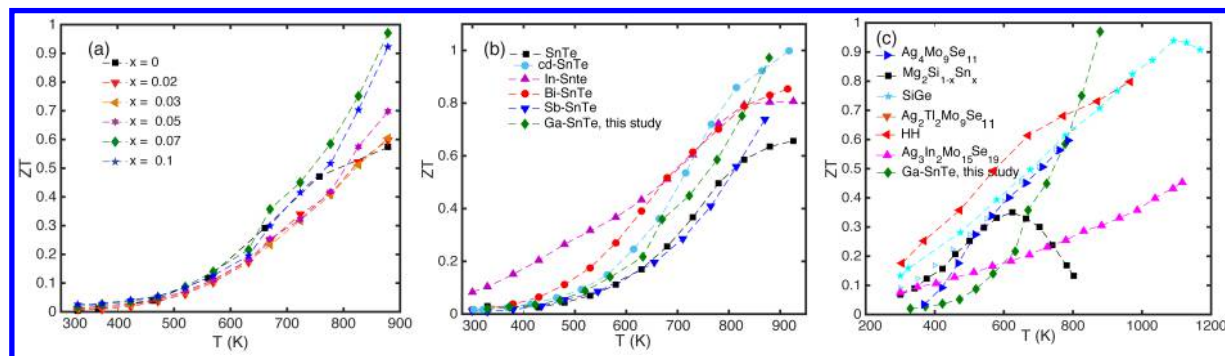


Figure 7: (a) The thermoelectric figure of merit ( $ZT$ ) as a function of temperature for  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  ( $x = 0, 0.02, 0.03, 0.05, 0.07$  and  $0.1$ ) samples. (b) Comparison of  $ZT$  values for pure SnTe, In-,<sup>43</sup> Cd-,<sup>38</sup>, Bi-doped<sup>44</sup>, Sb-doped<sup>54</sup> systems, and our results for Ga-doping SnTe, (c) Comparison of  $ZT$  of Ga-doped SnTe (this study) with some the best  $p$ -type lead-free thermoelectric materials including skutterudites,<sup>63</sup>  $\text{AgSn}_x\text{SbTe}_{2+x}$ ,<sup>64</sup>  $\text{Mg}_2\text{Si}_{1+x}\text{Sn}_x$ ,<sup>65</sup> Si-Ge alloy,<sup>66</sup> complex molybdenum chalcogenide<sup>15-17</sup> and half-Heusler<sup>67</sup> materials.

## Conclusions

We have synthesized high quality samples of Ga-doped SnTe spanning Ga concentration from 2% to 10%. The substitution of Sn with Ga lower substantially the lattice thermal conductivity to the point of reaching the amorphous limit at high temperature with 7-10% Ga-doping. The phenomenon is understood by XRD and SEM/EDS analysis that indicate the formation of GaTe nano-precipitates. Remarkably, the electronic transport properties are also improved by Ga-doping due to the activation of several hole pockets in the valence band as indicated by first principles calculations. The combination of ultra-low lattice thermal conductivity with power factors in excess of  $25 \text{ Wcm}^{-1}\text{K}^{-2}$  at high temperature increased the figure of merit,  $ZT$ , from 0.40 in pristine SnTe to  $\sim 1$  in 7% Ga-doped SnTe samples. The improved performances make Ga-doped SnTe a serious candidate for medium temperature thermoelectric power generation when toxic-free materials are desired.

## Acknowledgement

R. A. R. A. O. and D. W. thank Solvay Special Chemicals for financial support. This work was partially supported by Mid-career Researcher Program (No. 2011-0028729) and Nano.Material Technology Development Program (No. 2011-0030147) through the National Research Foundation of Korea (NRF) grant funded by the Ministry of Education, Science and Technology (MEST). Computations were performed at the Institut des Sciences Chimiques de Rennes and at the High Performance Computing Center, Michigan State University. M. F. acknowledges collaboration with the AFLOW Consortium (<http://www.aflow.org>) under the sponsorship of DOD-ONR (N000141310635 and N000141512266).

## Supporting Information Available

Input parameters for the calculation based on the Klemens; model at 300 K, thermal diffusivity, calculated Lorenz number as a function of  $x$  for  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  ( $x = 0, 0.02, 0.03, 0.05, 0.07$  and  $0.09$ ); thermoelectric properties of  $\text{Sn}_{0.96}\text{Ga}_{0.07}\text{Te}$  sample of initial and reproduced measurement; total electronic band structure on function of BZ of  $\text{Sn}_{32}\text{Te}_{32}$ , and  $\text{Sn}_{30}\text{Ga}_2\text{Te}_{32}$  cubic supercells; Powder XRD patterns for  $\text{Sn}_{1.03-x}\text{Ga}_x\text{Te}$  ( $x = 0, 0.02, 0.03, 0.05, 0.07$  and  $0.09$ ) samples. This material is available free of charge via the Internet at <http://pubs.acs.org/>.

## References

- (1) Snyder, G. J.; Toberer, E. S. Complex Thermoelectric Materials. *Nat. Mater* **2008**, *7*, 105–114.
- (2) Slack, G. A., Ed. *in Thermoelectrics Handbook : Macro to Nano, Eds., D. M. Rowe, CRC Press; 1995.*
- (3) Koumoto, T., K. and Mori, Ed. *In Thermoelectric Nanomaterials; 2013.*

- 1  
2  
3  
4 (4) Nolas, G. S.; Sharp, J.; Goldsmid, J. *Thermoelectrics: Basic Principles and New Ma-*  
5 *terials Developments*; Springer Series in Materials Science: Berlin, 2001; Vol. 45.  
6  
7  
8  
9 (5) Banik, A.; Shenoy, U. S.; Anand, S.; Waghmare, U. V.; Biswas, K. Mg Alloying in  
10 SnTe Facilitates Valence Band Convergence and Optimizes Thermoelectric Properties.  
11 *Chem. Mater.* **2015**, *27*, 581–587.  
12  
13  
14  
15 (6) Tan, G.; Shi, F.; Doak, J. W.; Sun, H.; Zhao, L.-D.; Wang, P.; Uher, C.; Wolver-  
16 ton, C.; Dravid, V. P.; Kanatzidis, M. G. Extraordinary role of Hg in enhancing the  
17 thermoelectric performance of p-type SnTe. *Energy Environ. Sci.* **2015**, *8*, 267–277.  
18  
19  
20  
21  
22 (7) Tan, G.; Shi, F.; Hao, S.; Chi, H.; Bailey, T. P.; Zhao, L.-D.; Uher, C.; Wolverton, C.;  
23 Dravid, V. P.; Kanatzidis, M. G. Valence Band Modification and High Thermoelectric  
24 Performance in SnTe Heavily Alloyed with MnTe. *J. Am. Chem. Soc.* **2015**, *137*, 11507–  
25 11516.  
26  
27  
28  
29  
30  
31 (8) Wu, H.; Chang, C.; Feng, D.; Xiao, Y.; Zhang, X.; Pei, Y.; Zheng, L.; Wu, D.; Gong, S.;  
32 Chen, Y.; He, J.; Kanatzidis, M. G.; Zhao, L.-D. Synergistically optimized electrical  
33 and thermal transport properties of SnTe via alloying high-solubility MnTe. *Energy*  
34 *Environ. Sci.* **2015**, *8*, 3298–3312.  
35  
36  
37  
38  
39  
40 (9) Al Rahal Al Orabi, R.; Mecholsky, N. A.; Hwang, J.; Kim, W.; Rhyee, J.-S.; Wee, D.;  
41 Fornari, M. Band Degeneracy, Low Thermal Conductivity, and High Thermoelectric  
42 Figure of Merit in SnTe-CaTe Alloys. *Chem. Mater.* **2016**, *28*, 376–384.  
43  
44  
45  
46  
47 (10) Tanryverdiev, V. S.; Aliev, O. M. Restoring the Density-Gradient Expansion for Ex-  
48 change in Solids and Surfaces. *Inorg. Mater.* **1995**, *31*, 1362.  
49  
50  
51  
52 (11) Carrete, J.; Li, W.; Mingo, N.; Wang, S.; Curtarolo, S. Finding Unprecedentedly Low-  
53 Thermal-Conductivity Half-Heusler Semiconductors via High-Throughput Materials  
54 Modeling. *Phys. Rev. X* **2014**, *4*, 011019.  
55  
56  
57  
58  
59  
60

- 1  
2  
3  
4 (12) Biswas, K.; He, J.; Wang, G.; Lo, S.-H.; Uher, C.; Dravid, V. P.; Kanatzidis, M. G.  
5 High Thermoelectric Figure of Merit in Nanostructured p-Type PbTe-MTe (M = Ca,  
6 Ba). *Energy Environ. Sci.* **2011**, *4*, 4675–4684.  
7  
8  
9  
10 (13) Wang, H.; Bahk, J.-H.; Kang, C.; Hwang, J.; Kim, K.; Shakouri, A.; Kim, W. Large  
11 Enhancement in the Thermoelectric Properties of Pb<sub>0.98</sub>Na<sub>0.02</sub>Te by Optimizing the  
12 Synthesis Conditions. *J. Mater. Chem. A* **2013**, *1*, 11269–11278.  
13  
14  
15  
16  
17 (14) Wang, H.; Bahk, J.-H.; Kang, C.; Hwang, J.; Kim, K.; Kim, J.; Burke, P.; Bowers, J. E.;  
18 Gossard, A. C.; Shakouri, A.; Kim, W. Right Sizes of Nano- and Microstructures for  
19 High-Performance and Rigid Bulk Thermoelectrics. *Proc. Natl. Acad. Sci.* **2014**, *111*,  
20 10949–10954.  
21  
22  
23  
24  
25  
26 (15) Al Rahal Al Orabi, R.; Gougeon, P.; Gall, P.; Fontaine, B.; Gautier, R.; Colin, M.;  
27 Candolfi, C.; Dauscher, A.; Hejtmanek, J.; Malaman, B.; Lenoir, B. X-ray Charac-  
28 terization, Electronic Band Structure, and Thermoelectric Properties of the Cluster  
29 Compound Ag<sub>2</sub>Tl<sub>2</sub>Mo<sub>9</sub>Se<sub>11</sub>. *Inorg. Chem.* **2014**, *53*, 11699–11709.  
30  
31  
32  
33  
34  
35 (16) Zhou, T.; Lenoir, B.; Colin, M.; Dauscher, A.; Al Rahal Al Orabi, R.; Gougeon, P.;  
36 Potel, M.; Guilmeau, E. Promising thermoelectric properties in Ag<sub>x</sub>Mo<sub>9</sub>Se<sub>11</sub> compounds  
37 (3.4 ≤ x ≤ 3.9). *App. Phys. Lett.* **2011**, *98*.  
38  
39  
40  
41  
42 (17) Gougeon, P.; Gall, P.; Al Rahal Al Orabi, R.; Fontaine, B.; Gautier, R.; Potel, M.;  
43 Zhou, T.; Lenoir, B.; Colin, M.; Candolfi, C.; Dauscher, A. Synthesis, Crystal and  
44 Electronic Structures, and Thermoelectric Properties of the Novel Cluster Compound  
45 Ag<sub>3</sub>In<sub>2</sub>Mo<sub>15</sub>Se<sub>19</sub>. *Chem. Mater.* **2012**, *24*, 2899–2908.  
46  
47  
48  
49  
50  
51 (18) Al Rahal Al Orabi, R.; Fontaine, B.; Gautier, R.; Gougeon, P.; Gall, P.; Bouyrie, Y.;  
52 Dauscher, A.; Candolfi, C.; Lenoir, B. Cu Insertion Into the Mo<sub>12</sub> Cluster Compound  
53 Cs<sub>2</sub>Mo<sub>12</sub>Se<sub>14</sub>: Synthesis, Crystal and Electronic Structures, and Physical Properties.  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3  
4 (19) Vaqueiro, P.; Al Rahal Al Orabi, R.; Luu, S. D. N.; Guelou, G.; Powell, A. V.;  
5 Smith, R. I.; Song, J.-P.; Wee, D.; Fornari, M. The role of copper in the thermal  
6 conductivity of thermoelectric oxychalcogenides: do lone pairs matter? *Phys. Chem.*  
7 *Chem. Phys.* **2015**, *17*, 31735–31740.
- 8  
9  
10  
11  
12 (20) Wee, D.; Kozinsky, B.; Marzari, N.; Fornari, M. Effects of filling in CoSb<sub>3</sub>: Local  
13 structure, band gap, and phonons from first principles. *Phys. Rev. B* **2010**, *81*, 045204.
- 14  
15  
16  
17 (21) Bang, S.; Wee, D.; Li, A.; Fornari, M.; Kozinsky, B. Thermoelectric properties of  
18 pnictogen-substituted skutterudites with alkaline-earth fillers using first-principles cal-  
19 culations. *J. Appl. Phys.* **2016**, *119*.
- 20  
21  
22  
23  
24 (22) Al Rahal Al Orabi, R.; Orisakwe, E.; Wee, D.; Fontaine, B.; Gautier, R.; Halet, J.-  
25 F.; Fornari, M. Prediction of high thermoelectric potential in AMN<sub>2</sub> layered nitrides:  
26 electronic structure, phonons, and anharmonic effects. *J. Mater. Chem. A* **2015**, *3*,  
27 9945–9954.
- 28  
29  
30  
31  
32  
33 (23) Biswas, K.; He, J.; Blum, I. D.; Wu, C.-I.; Hogan, T. P.; Seidman, D. N.; Dravid, V. P.;  
34 Kanatzidis, M. G. High-Performance Bulk Thermoelectrics With All-Scale Hierarchical  
35 Architectures. *Nature* **2012**, *489*, 414–418.
- 36  
37  
38  
39  
40 (24) Biswas, K.; He, J.; Zhang, Q.; Wang, G.; Uher, C.; Dravid, V. P.; Kanatzidis, M. G.  
41 Strained Endotaxial Nanostructures With High Thermoelectric Figure of Merit. *Nat.*  
42 *Chem.* **2012**, *3*, 160–166.
- 43  
44  
45  
46  
47 (25) Wang, H.; Hwang, J.; Snedaker, M. L.; Kim, I.-h.; Kang, C.; Kim, J.; Stucky, G. D.;  
48 Bowers, J.; Kim, W. High Thermoelectric Performance of a Heterogeneous PbTe  
49 Nanocomposite. *Chem. Mater.* **2015**, *27*, 944–949.
- 50  
51  
52  
53  
54 (26) Gelbstein, Y.; Rosenberg, Y.; Sadia, Y.; Dariel, M. P. Thermoelectric Properties Evolu-  
55 tion of Spark Plasma Sintered (Ge<sub>0.6</sub>Pb<sub>0.3</sub>Sn<sub>0.1</sub>)Te Following a Spinodal Decomposition.  
56 *J. Phys. Chem. C* **2010**, *114*, 13126–13131.
- 57  
58  
59  
60

- 1  
2  
3  
4 (27) Gelbstein, Y.; Dashevsky, Z.; Dariel, M. P. Highly efficient bismuth telluride doped  
5 p-type  $\text{Pb}_{0.13}\text{Ge}_{0.87}\text{Te}$  for thermoelectric applications. *Phys. Stat. Sol. RRL* **2007**, *1*,  
6 232–234.  
7  
8  
9  
10 (28) Gelbstein, Y.; Davidow, J.; Girard, S. N.; Chung, D. Y.; Kanatzidis, M. Controlling  
11 Metallurgical Phase Separation Reactions of the  $\text{Ge}_{0.87}\text{Pb}_{0.13}\text{Te}$  Alloy for High Ther-  
12 moelectric Performance. *Adv. Energy Mater.* **2013**, *3*, 815–820.  
13  
14  
15  
16  
17 (29) Zhao, L. D.; Wu, H. J.; Hao, S. Q.; Wu, C. I.; Zhou, X. Y.; Biswas, K.; He, J. Q.;  
18 Hogan, T. P.; Uher, C.; Wolverton, C.; Dravid, V. P.; Kanatzidis, M. G. All-Scale  
19 Hierarchical Thermoelectrics:  $\text{MgTe}$  in  $\text{PbTe}$  Facilitates Valence Band Convergence  
20 and Suppresses Bipolar Thermal Transport for High Performance. *Energy Environ.*  
21 *Sci.* **2013**, *6*, 3346–3355.  
22  
23  
24  
25  
26  
27  
28 (30) Ginting, D.; Lin, C.-C.; Rathnam, L.; Yu, B.-K.; Kim, S.-J.; Al Rahal Al Orabi, R.;  
29 Rhyee, J.-S. Enhancement of thermoelectric properties by effective K-doping and nano  
30 precipitation in quaternary compounds of  $(\text{Pb}_{1-x}\text{K}_x\text{Te})_{0.70}(\text{PbSe})_{0.25}(\text{PbS})_{0.05}$ . *RSC*  
31 *Adv.* **2016**, *6*, 62958–62967.  
32  
33  
34  
35  
36  
37 (31) Zhao, L.-D.; Lo, S.-H.; Zhang, Y.; Sun, H.; Tan, G.; Uher, C.; Wolverton, C.;  
38 Dravid, V. P.; Kanatzidis, M. G. Ultralow thermal conductivity and high thermoelectric  
39 figure of merit in  $\text{SnSe}$  crystals. *Nature* **2015**, *508*, 373–377.  
40  
41  
42  
43  
44 (32) Zhao, L.-D.; Tan, G.; Hao, S.; He, J.; Pei, Y.; Chi, H.; Wang, H.; Gong, S.; Xu, H.;  
45 Dravid, V. P.; Uher, C.; Snyder, G. J.; Wolverton, C.; Kanatzidis, M. G. Ultrahigh  
46 power factor and thermoelectric performance in hole-doped single-crystal  $\text{SnSe}$ . *Science*  
47 **2016**, *351*, 141–144.  
48  
49  
50  
51  
52  
53 (33) Vedeneev, V.; Krivoruchko, S.; Sabo, E. Tin Telluride Based Thermoelectrical Alloys.  
54 *Semiconductors* **1998**, *32*, 241–244.  
55  
56  
57  
58  
59  
60

- 1  
2  
3  
4 (34) Rogers, L. M. High Thermoelectric Performance of a Heterogeneous PbTe Nanocom-  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16 (35) He, J.; Xu, J.; Liu, G.-Q.; Shao, H.; Tan, X.; Liu, Z.; Xu, J.; Jiang, H.; Jiang, J. En-  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60
- (34) Rogers, L. M. High Thermoelectric Performance of a Heterogeneous PbTe Nanocom-  
posite. *J. Phys. D: Appl. Phys.* **1968**, *1*, 845.
- (35) He, J.; Xu, J.; Liu, G.-Q.; Shao, H.; Tan, X.; Liu, Z.; Xu, J.; Jiang, H.; Jiang, J. En-  
hanced thermopower in rock-salt SnTe-CdTe from band convergence. *RSC Adv.* **2016**,  
*6*, 32189–32192.
- (36) Esaki, L.; Stiles, P. J. New Type of Negative Resistance in Barrier Tunneling. *Phys.*  
*Rev. Lett.* **1966**, *16*, 1108–1111.
- (37) Dimmock, J. O.; Melngailis, I.; Strauss, A. J. Band Structure and Laser Action in  
Pb<sub>x</sub>Sn<sub>1-x</sub>Te. *Phys. Rev. Lett.* **1966**, *16*, 1193–1196.
- (38) Tan, G.; Zhao, L.-D.; Shi, F.; Doak, J. W.; Lo, S.-H.; Sun, H.; Wolverton, C.;  
Dravid, V. P.; Uher, C.; Kanatzidis, M. G. High Thermoelectric Performance of p-  
Type SnTe via a Synergistic Band Engineering and Nanostructuring Approach. *J. Am.*  
*Chem. Soc.* **2014**, *136*, 7006–7017.
- (39) He, J.; Tan, X.; Xu, J.; Liu, G.-Q.; Shao, H.; Fu, Y.; Wang, X.; Liu, Z.; Xu, J.; Jiang, H.;  
Jiang, J. Valence band engineering and thermoelectric performance optimization in  
SnTe by Mn-alloying via a zone-melting method. *J. Mater. Chem. A* **2015**, *3*, 19974–  
19979.
- (40) Tan, X. J.; Liu, G. Q.; Xu, J. T.; Shao, H. Z.; Jiang, J.; Jiang, H. C. Element-selective  
resonant state in M-doped SnTe (M = Ga, In, and Tl). *Phys. Chem. Chem. Phys.*  
**2016**, *18*, 20635–20639.
- (41) Tan, X. J.; Shao, H. Z.; He, J.; Liu, G. Q.; Xu, J. T.; Jiang, J.; Jiang, H. C. Band  
engineering and improved thermoelectric performance in M-doped SnTe (M = Mg, Mn,  
Cd, and Hg). *Phys. Chem. Chem. Phys.* **2016**, *18*, 7141–7147.



- 1  
2  
3  
4 (42) Tan, G.; Zeier, W. G.; Shi, F.; Wang, P.; Snyder, G. J.; Dravid, V. P.; Kanatzidis, M. G.  
5 High Thermoelectric Performance SnTe-In<sub>2</sub>Te<sub>3</sub> Solid Solutions Enabled by Resonant  
6 Levels and Strong Vacancy Phonon Scattering. *Chem. Mater.* **2015**, *27*, 7801–7811.  
7  
8  
9  
10 (43) Zhang, Q.; Liao, B.; Lan, Y.; Lukas, K.; Liu, W.; Esfarjani, K.; Opeil, C.; Broido, D.;  
11 Chen, G.; Ren, Z. High Thermoelectric Performance by Resonant Dopant Indium in  
12 Nanostructured SnTe. *Proc. Natl. Acad. Sci. U. S. A.* **2013**, *110*, 13261–13266.  
13  
14  
15  
16  
17 (44) Zhao, L.-D.; Zhang, X.; Wu, H.; Tan, G.; Pei, Y.; Xiao, Y.; Chang, C.; Wu, D.; Chi, H.;  
18 Zheng, L.; Gong, S.; Uher, C.; He, J.; Kanatzidis, M. G. Enhanced Thermoelectric  
19 Properties in the Counter-Doped SnTe System with Strained Endotaxial SrTe. *J. Am.*  
20 *Chem. Soc.* **2016**, *138*, 2366–2373.  
21  
22  
23  
24  
25  
26 (45) Tan, G.; Shi, F.; Hao, S.; Chi, H.; Zhao, L.-D.; Uher, C.; Wolverton, C.; Dravid, V. P.;  
27 Kanatzidis, M. G. Codoping in SnTe: Enhancement of Thermoelectric Performance  
28 through Synergy of Resonance Levels and Band Convergence. *J. Am. Chem. Soc.* **2015**,  
29 *137*, 5100–5112.  
30  
31  
32  
33  
34  
35 (46) Tan, G.; Shi, F.; Sun, H.; Zhao, L.-D.; Uher, C.; Dravid, V. P.; Kanatzidis, M. G.  
36 SnTe-AgBiTe<sub>2</sub> as an efficient thermoelectric material with low thermal conductivity. *J.*  
37 *Mater. Chem. A* **2014**, *2*, 20849–20854.  
38  
39  
40  
41  
42 (47) Zhang, Q.; Cao, F.; Lukas, K.; Liu, W.; Esfarjani, K.; Opeil, C.; Broido, D.; Parker, D.;  
43 Singh, D. J.; Chen, G.; Ren, Z. Study of the Thermoelectric Properties of Lead Selenide  
44 Doped with Boron, Gallium, Indium, or Thallium. *J. Am. Chem. Soc.* **2012**, *134*,  
45 17731–17738.  
46  
47  
48  
49  
50  
51 (48) Wagner, M. heat-specific. *These de Doctorat, Universitat Wien* **2007**,  
52  
53  
54 (49) Blaha, P.; Schwarz, K.; Madsen, G. K. H.; Kvasnicka, D.; Luitz, J. *WIEN2K, An*  
55 *Augmented Plane Wave + Local Orbitals Program for Calculating Crystal Properties*;  
56 Karlheinz Schwarz, Techn. Universität Wien, Austria, 2001.  
57  
58  
59  
60

- 1  
2  
3  
4 (50) Tran, F.; Blaha, P. Accurate Band Gaps of Semiconductors and Insulators with a  
5 Semilocal Exchange-Correlation Potential. *Phys. Rev. Lett.* **2009**, *102*, 226401.  
6  
7  
8 (51) May, A. F.; Toberer, E. S.; Saramat, A.; Snyder, G. J. Characterization and analysis of  
9 thermoelectric transport in *n*-type  $\text{Ba}_8\text{Ga}_{16-x}\text{Ge}_{30+x}$ . *Phys. Rev. B* **2009**, *80*, 125205.  
10  
11  
12 (52) Cahill, D. G.; Watson, S. K.; Pohl, R. O. Lower Limit to the Thermal Conductivity of  
13 Disordered Crystals. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1992**, *46*, 6131–6140.  
14  
15  
16 (53) Tan, G.; Shi, F.; Hao, S.; Zhao, L.-D.; Chi, H.; Zhang, X.; Uher, C.; Wolverton, C.;  
17 Dravid, V. P.; Kanatzidis, M. G. Non-equilibrium processing leads to record high ther-  
18 moelectric figure of merit in PbTe-SrTe. *Nat. Commun.* **2016**, *7*, 12167.  
19  
20  
21 (54) Banik, A.; Vishal, B.; Perumal, S.; Datta, R.; Biswas, K. The origin of low thermal  
22 conductivity in  $\text{Sn}_{1-x}\text{Sb}_x\text{Te}$ : phonon scattering via layered intergrowth nanostructures.  
23 *Energy Environ. Sci.* **2016**, *9*, 2011–2019.  
24  
25  
26 (55) Abeles, B. Lattice Thermal Conductivity of Disordered Semiconductor Alloys at High  
27 Temperatures. *Phys. Rev.* **1963**, *131*, 1906–1911.  
28  
29  
30 (56) Eshelby, J. D. Lattice Thermal Conductivity of Disordered Semiconductor Alloys at  
31 High Temperatures. *Acta Metall.* **1955**, *3*, 487.  
32  
33  
34 (57) Klemens, P. G. Thermal Resistance due to Point Defects at High Temperatures. *Phys.*  
35 *Rev.* **1960**, *119*, 507–509.  
36  
37  
38 (58) Toberer, E. S.; Zevalkink, A.; Crisosto, N.; , G. J. The Zintl Compound  $\text{Ca}_5\text{Al}_2\text{Sb}_6$  for  
39 Low-Cost Thermoelectric Power Generation. *Adv. Funct. Mater.* **2010**, *20*, 4375–4380.  
40  
41  
42 (59) Pei, Y.; LaLonde, A.; Iwanaga, S.; Snyder, G. J. High thermoelectric figure of merit in  
43 heavy hole dominated PbTe. *Energy Environ. Sci.* **2011**, *4*, 2085–2089.  
44  
45  
46 (60) Goldsmid, H.; Sharp, J. Estimation of the Thermal Band Gap of a Semiconductor From  
47 Seebeck Measurements. *J. Electron. Mater.* **1999**, *28*, 869–872.  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3  
4 (61) Brebrick, R. F.; Strauss, A. J. Anomalous Thermoelectric Power as Evidence for Two-  
5 Valence Bands in SnTe. *Phys. Rev.* **1963**, *131*, 104–110.  
6  
7  
8  
9 (62) Brebrick, R. Deviations From Stoichiometry and Electrical Properties in SnTe. *J. Phys.*  
10 *Chem. Solids* **1963**, *24*, 27 – 36.  
11  
12  
13 (63) Tan, G.; Zheng, Y.; Tang, X. Semiconducting Ge Clathrates: Promising Candidates  
14 for Thermoelectric Applications. *Appl. Phys. Lett.* **2013**, *103*, 183904.  
15  
16  
17  
18 (64) Han, M.-K.; Androulakis, J.; Kim, S.-J.; Kanatzidis, M. G. Lead-Free Thermoelectrics:  
19 High Figure of Merit in p-type  $\text{AgSn}_m\text{SbTe}_{m+2}$ . *Adv. Energy Mater.* **2012**, *2*, 157–161.  
20  
21  
22  
23 (65) Liu, W.; Yin, K.; Su, X.; Li, H.; Yan, Y.; Tang, X.; Uher, C. Enhanced Hole Concentra-  
24 tion Through Ga Doping and Excess of Mg and Thermoelectric Properties of p-Type  
25  $\text{Mg}_{2(1+z)}(\text{Si}_{0.3}\text{Sn}_{0.7})_y\text{Ga}_y$ . *Intermetallics* **2013**, *32*, 352 – 361.  
26  
27  
28  
29  
30 (66) Joshi, G.; Lee, H.; Lan, Y.; Wang, X.; Zhu, G.; Wang, D.; Gould, R. W.; Cuff, D. C.;  
31 Tang, M. Y.; Dresselhaus, M. S.; Chen, G.; Ren, Z. Enhanced Thermoelectric Figure-  
32 of-Merit in Nanostructured p-type Silicon Germanium Bulk Alloys. *Nano Letters* **2008**,  
33 *8*, 4670–4674.  
34  
35  
36  
37  
38  
39 (67) Yan, X.; Joshi, G.; Liu, W.; Lan, Y.; Wang, H.; Lee, S.; Simonson, J. W.; Poon, S. J.;  
40 Tritt, T. M.; Chen, G.; Ren, Z. F. Enhanced Thermoelectric Figure of Merit of p-Type  
41 Half-Heuslers. *Nano Letters* **2011**, *11*, 556–560.  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

## Graphical TOC Entry

